

VISCARIA
Exploration Results

PERC (2021)
Reporting standard
Table 1

September 2024

Table of Contents

PERC REPORTING STANDARD - TABLE 1	1
Appendix 1 – Figures	i
Appendix 2 – Tables	vii
Appendix 3 – References	xlvi
Appendix 4 – Certificate of Competent Person.....	xlix

List of Figures

Figure 1. Geological structural map of Norrbotten showing the location of the Viscaria deposit. Modified after Berman et al 2001.....	ii
Figure 2. Overview map of Viscaria Kiruna AB’s tenures effective date 20240912. Exploitation concessions (bearbetningskoncessioner) marked in green and Exploration permits (undersökningstillstånd) outlined in blue.	iii
Figure 3. Satellite map of Viscaria area showing drillhole traces declared in the exploration results relative to mineralized zones (orange).	iv
Figure 4. Top view showing drillhole IDs and traces in relation to models of the mineralized zones in Viscaria.	v
Figure 5: Side view showing orebodies A, B, D with drillhole traces. Facing NE.	vi

List of Tables

Table 1. Collar table of drillholes.....	viii
Table 2. Assay results.....	ix

Section References	PERC REPORTING STANDARD - TABLE 1			Section in the CPR where this is located or why it is considered not relevant to the project (“if not, why not”).
	Exploration Results	Mineral Resources	Mineral Reserves	

Section 1: Project Outline				
		1.0 Introduction - General		
Section 1: Project Outline	1.0	(i)	The terms of reference or scope of work.	Reporting of PERC (2021) compliant Exploration Results from the Viscaria deposit located in Kiruna, Sweden. The report is prepared by Gruvaktiebolaget Viscaria and evaluated by an independent Competent Person, Thomas Lindholm, GeoVista AB. Reporting includes the company's most recent results from the near mine exploration campaigns performed in 2023 and 2024. The program has been performed close to existing Mineral Resource. The report is including exploration results but exclusive of an updated mineral resource declaration. Reporting includes a newly discovered mineralized zone, ABBA zone, as well as extensions of existing mineralized zones. The report covers in total 21 new drillholes (4 with ongoing drilling/logging), for a total of 12,500 meters at time of writing.
		(ii)	The Competent Person’s relationship to the issuer of the report, if any.	Independent Competent Person, Thomas Lindholm, GeoVista AB.
		(iii)	A statement for whom the report was prepared; whether it was intended as a full or partial evaluation or other purpose, work conducted, effective date of report, and remaining work.	The Exploration results in Table 1 were prepared by Gruvaktiebolaget Viscaria with effective date of release 20240924.
		(iv)	Sources of information and data contained in the report or used in its preparation, with citations if applicable, and a list of references.	See Appendix 1.2, and 3
		(v)	A title page and a table of contents that includes figures and tables.	See the Title Page and Table of Contents
		(vi)	An Executive Summary, which briefly summarises important information in the public report, including property description and ownership, geology and mineralisation, the status of exploration, development and operations, Mineral Resource and Mineral Reserve estimates, and the Competent Person's conclusions and recommendations. If Inferred Mineral Resources are used, a summary valuation with and if practical without inclusion of such Inferred Mineral Resources. The Executive Summary should have sufficient detail to allow the reader to understand the essentials of the project.	N/A
		(vii)	A declaration from the Competent Person, stating whether “the declaration has been made in terms of the guidelines of the PERC Reporting Standard”.	Certificate of Competent Person

		(viii)	Diagrams, maps, plans, sections and illustrations, which are dated, legible and prepared at an appropriate scale to distinguish important features. Maps including a legend, author or information source, coordinate system and datum, a scale in bar or grid form, and an arrow indicating north. Reference to a location or index map and more detailed maps showing all important features described in the text, including all relevant cadastral and other infrastructure features.	See Appendix. 1 – Figures
		(ix)	The units of measure, currency and relevant exchange rates.	N/A
		(x)	The details of the personal inspection on the property by each Competent Person or, if applicable, the reason why a personal inspection has not been completed.	The Competent Person last visited the site in August 2024 and was given plenty of opportunity to inspect the drillcore in question and discuss the results with the company’s geologists.
		(xi)	If the Competent Person is relying on a report, opinion, or statement of another expert who is not a Competent Person, then a disclosure of the date, title, and author of the report, opinion, or statement, the qualifications of the other expert, the reason for the Competent Person to rely on the other expert, any significant risks and any steps the Competent Person took to verify the information provided.	N/A
		1.1 Property Description		
1.1	(i)	Brief description of the scope of project (i.e. whether in preliminary sampling, advanced exploration, scoping, pre-feasibility, or feasibility phase, Life of Mine plan for an ongoing mining operation or closure).		The Viscaria mine is in feasibility study phase, with a planned mine opening in 2026.
	(ii)	Describe (noting any conditions that may affect possible prospecting/mining activities) topography, elevation, drainage, fauna and flora, the means and ease of access to the property, the proximity of the property to a population centre, and the nature of transport, the climate, known associated climatic risks and the length of the operating season and to the extent relevant to the mineral project, the sufficiency of surface rights for mining operations including the availability and sources of power, water, mining personnel, potential tailings storage areas, potential waste disposal areas, heap leach pad areas, and potential processing plant sites.		The location of the mine site, 150 km north of the arctic circle and 250 km east of the North Atlantic Sea strongly affects the climate in the area. February has the lowest temperature down to average -21° C. The warmest month is July, when the temperature normally varies between 9,2° C to 17,6° C. Precipitation is greatest during the summer months with an average value of 94 mm during the month of July, followed by August with 68 mm. The snow depth average is 75 cm, and snow and ice cover the landscape and lakes from October to May. The melting of the frozen precipitation results in a short and intensive spring flood normally lasting a few weeks in May to June. The average value of the wind speed at Kiruna Airport measuring station is 3,5 m/s and the dominating wind direction is from south to southwest. Mining in subarctic conditions means climatic risk for machinery and labour force, but 100 years of mining tradition in the surrounding underground and open pits has developed modern technology and working conditions that are very well adapted for the environmental conditions. Water supply and mine drainage systems must be adapted to arctic dry periods during winter and high flows

					during late spring and summer, to support process- and drilling water. (Table 1, November 2022) Viscaria Kiruna AB has built a new bridge and road to the area to support the establishment of the mine. The location of the mine near LKAB Kiirunavaara means infrastructure and workforce are well adapted to underground mining. See Section 1.0 (x) of this Table 1.	
		(iii)	Specify the details of the personal inspection on the property by each CP or, if applicable, the reason why a personal inspection has not been completed.			
			1.2 Location			
Section 1: Project Outline	1.2	(i)	Description of location and map (country, province, and closest town/city, coordinate systems and ranges, etc.).		The A, B and D Zones of the Viscaria Copper Project (the Project) are located in Kiruna municipality (population 23,500), in Norrbotten County, the northernmost County in Sweden, approximately 150 km north of the Arctic Circle. The project lies approximately 5 km northwest of the town of Kiruna. The Project is located 270 km north-northwest of the port city of Luleå, which lies on the Gulf of Bothnia in the north of the Baltic Sea and 130 km southeast of the port city of Narvik in northern Norway. (Table 1, November 2022) Coordinate system is SWEREF 99 2015	
		(ii)	Country Profile: describe information pertaining to the project host country that is pertinent to the project, including relevant applicable legislation, environmental and social context etc. Assess, at a high level, relevant technical, environmental, social, economic, political and other key risks.		See company's webpage www.viscaria.com	
		(iii)	Provide a general topocadastral map	Provide a Topo-cadastral map in sufficient detail to support the assessment of eventual economics. State the known associated climatic risks.	Provide a detailed Topo-cadastral map. Confirm that applicable aerial surveys have been checked with ground controls and surveys, particularly in areas of rugged terrain, dense vegetation or high altitude.	See Appendix. 1 – Figures
				1.3 Adjacent Properties		
		1.3	(i)	Discuss details of relevant adjacent properties. If adjacent or nearby properties have an important bearing on the report, then their location and common mineralized structures should be included on the maps. Reference all information used from other sources.		Neighbouring Kiirunavaara world known Fe deposit is likely related to the Viscaria deposit.
			1.4 History			

1.4	(i)	State historical background to the project and adjacent areas concerned, including known results of previous exploration and mining activities (type, amount, quantity and development work), previous ownership and changes thereto.		<p>No mining of the D zone (and little in B zone) have been completed yet and hence there is no reconciliation information available.</p> <p>In the A zone during 1982-1997, 15 years of mining with 12.5Mt @ 2.3% Cu was done (primarily). Experience from the past mining improves the technical knowledge of planned mining operation at the B and D zone.</p> <p>Several JORC compliant mineral resource updates have been completed for the Viscaria project.</p> <p>Successful mining operation was completed 1982-1997. The Viscaria Project has hereafter, systematically worked towards reopening the Viscaria mine-and the acquisition by Copperstone of Viscaria in 2019 is deemed to be the most ambitious one.</p> <p>(Table 1 November 2022)</p>
	(ii)	Present details of previous successes or failures with reasons why the project may now be considered potentially economic.		Old Viscaria mine closed due to low copper prices. The current price is much higher and projected to stay high.
	(iii)		Discuss known or existing historical Mineral Resource estimates and performance statistics on actual production for past and current operations.	N/A
	(iv)			Discuss known or existing historical Mineral Reserve estimates and performance statistics on actual production for past and current operations.
		1.5 Legal Aspects and Permitting		
1.5	(i)	A statement from the Competent Person on the confirmation of the legal tenure, including a description of (the following):		The Competent Person has verified the company's tenure in the publicly available database at the Inspector of Mines office.
	(ii)	Discuss the nature of the issuer's rights (e.g. prospecting and/or mining) and the right to use the surface of the properties to which these rights relate. Disclose the date of expiry and other relevant details.		<p>Viscaria Kiruna AB has three granted exploitation concessions under the Minerals Act (SFS1991: 45); Viscaria K no 3 and K no 4 which were granted by Bergsstaten (Mining Inspectorate) in January 2012, both expiring 2037, and Viscaria K no 7 which was granted in March 2018, expiring 2043. (Table 1 November 2022)</p> <p>The exploration results presented are mainly from these concessions.</p> <p>If mining, development for mining or other significant work to continue extraction on-going at the time of expiry, the concessions will automatically be extended for a 10-year period.</p> <p>The area around the deposit is planned in detail for mining operations and designated as an area of national interest for deposits of valuable</p>

				minerals or materials that are of great importance for the country's supply readiness. (Table 1 November 2022) Viscaria Kiruna AB also has 11 exploration licenses surrounding the exploitation concessions. Map overview of Viscaria tenements Figure 2 .
		(iii)	Present the principal terms and conditions of all existing agreements, and details of those still to be obtained, (such as, but not limited to, concessions, partnerships, joint ventures, access rights, leases, historical and cultural sites, wilderness or national park and environmental settings, royalties, consents, permission, permits or authorisations).	See the company's tenures at www.viscaria.com
		(iv)	Present the security of the tenure held at the time of reporting or that is reasonably expected to be granted in the future along with any known impediments to obtaining the right to operate in the area. State details of applications that have been made. See Clause 8.1 for declaration of a Mineral Reserve.	See the company's tenures at www.viscaria.com
		(v)	Provide a statement of any legal proceedings for example, land claims, that may have an influence on the rights to prospect or mine for minerals, or an appropriate negative statement.	See the company's tenures at www.viscaria.com
		(vi)	Provide a statement relating to governmental/statutory requirements and permits as may be required, have been applied for, approved or can be reasonably be expected to be obtained. Provide a review of risks that permits will not be received as expected and impact of delays to the project.	Final environmental permit for mining is in appeals stage, the latest news on the status can be found on the company's webpage www.viscaria.com
			1.6 Royalties	
	1.6	(i)	Describe the royalties that are payable in respect of each property.	Mineral extraction fee of 0.2% applicable according to the Mineral's Act. A potential of maximum 1% net smelter royalty may apply within specific exploitation concession borders following earlier arrangements.
			1.7 Liabilities	
	1.7	(i)	Describe any liabilities, including rehabilitation guarantees that are pertinent to the project. Provide a description of the rehabilitation liability, including, but not limited to, legislative requirements, assumptions and limitations.	The mine area will have to be rehabilitated when operations cease. As a security bond of 344 MSEK will be deposited with the County Administrative Board. In the first phase a 60.6 MSEK bond was deposited in order to guarantee rehabilitation of the initial mine drainage and the water treatment plant.
	Section 2: Geological Setting, Deposit, Mineralisation			
			2.1 Geological Setting, Deposit Type and Mineralisation Style	
Section 2: Geological Setting, Deposit,	2.1	(i)	Describe the regional geology.	(Adapted from Mineral Resource Inventory Viscaria D-zone 30 Nov 2020) The Kiruna Greenstone Group is related to a rifting event that occurred between 2.2 Ga and 2.0 Ga. The Kiruna Greenstone Group forms part of the Karelian Suite and consists of a 2 km to 4 km thick

			<p>pile of subaerial and submarine basalt, andesite, tuffites, volcanoclastics and chemical sediments. The Viscaria Formation is part of the Kiruna Greenstone Group comprises a succession of volcanoclastic, chemical and organic sediments (carbon-rich shales). The Kiruna area is characterized by a low degree of metamorphism (generally upper greenschist to lower amphibolite facies) with well-preserved primary structures (Bergman et al. 2001).</p>
(ii)	Describe the project geology including mineral deposit type, geological setting and style of mineralisation.		<p>(Adapted from Mineral Resource Inventory Viscaria D-zone 30 Nov 2020)</p> <p>The Viscaria Formation hosts three distinct zones of stratiform to stratabound mineralisation that are referred to as D Zone, B Zone and A Zone (in lowest to highest stratigraphic order). The middle and upper parts of the Viscaria Formation, between the D Zone horizon and the A Zone horizon, has been intruded by several mafic sills. The sills range in thickness from 10 m to 50 m (Martinsson, 1997).</p> <p>The D Zone mineralisation broadly lies within the lowermost part of the Viscaria Formation which is defined by a strongly magnetite-replaced Ca-Mg-carbonate stratigraphic unit. The hanging wall to the D ore lens comprises talc, tremolite and chlorite altered tuffaceous sediments interbedded with cherty and graphitic siltstones.</p> <p>The B zone mineralization lies in a series of tuffites and pyroclastic beds with interbedded graphitic schists.</p> <p>The host rock of the A Zone mineralisation is composed of a mixture of tuffites and graphitic schist.</p> <p>Significant chalcopyrite mineralization occurs in A, B and D zone. Magnetite is present in all zones but is significant (minable) only in D zone.</p>
(iii)	Discuss the geological model or concepts being applied in the investigation and on the basis of which the exploration program is planned. Describe the inferences made from this model.		<p>Updates of the geological model and resource estimation update will be declared in coming mineral resource update. Published mineral resource from 2022 can be found on www.viscaria.com.</p>
(iv)	Discuss data density, distribution and reliability and whether the quality and quantity of information are sufficient to support statements, made or inferred, concerning the project.		<p>Results published in this Table 1 consists of a total of 21 new drillholes, all in close connection to existing declared resources of Viscaria, which should be sufficient for declaring exploration results. Gruvaktiebolaget Viscaria intend to follow up on the results with additional drilling and incorporate these results in the coming resource updates. 3 older drillholes are included for comparison.</p>
(v)	Discuss the significant minerals present in the deposit, their frequency, size and other characteristics. These include minor and gangue minerals where these will have an effect on the processing steps. Indicate the variability of each important mineral within the mineral deposit.		<p>Mineralogy for Viscaria deposit is described in Table 1 November 2022. More recent articles regarding mineral characterization can be found in and Imana M. et al 2023 and Tasbicen K. et al 2023.</p>

		(vi)	Describe the significant mineralised zones encountered on the property, including a summary of the surrounding rock types, relevant geological controls, and the length, width, depth, and continuity of the mineralisation, together with a description of the type, character, and distribution of the mineralisation	(From Table 1, November 2022) The D orebody is hosted within a thick carbonate unit (>15m). This unit shows magnetite chalcopyrite replacements along both margins. Localized talc and amphibole occur associated with low Cu grade areas. Elevated content of Fe oxides (22-26% of Fe hosted in magnetite) with Cu sulphides (chalcopyrite) and Fe sulphide (pyrite) replacing along magnetite grain boundaries and less in a marble Mg-rich amphibole unit. D zone has negligible contents of Fe and Zn sulphides. Peripheral or marginal zones have sparse pyrite replacement on magnetite. A barren to low Cu grade specular hematite zone occurs near the tectonic footwall of the marble unit. The A and B orebodies have several similarities in terms of their higher proportion of calcsilicate assemblages and bed parallel and crosscutting Cu and Fe sulphide veining. The A zone contains a carbonaceous graphitic ore type whereas B orebody normally contains Cu sulphide dissemination and veining in the peripheral biotite-altered zones. Both A and B orebodies are harder and more competent than D carbonate magnetite rich orebodies.
		(vii)	Confirm that reliable geological models and / or maps and cross sections that support interpretations exist.	See Appendix 1
Section 3: Exploration and Drilling, Sampling Techniques and Data				
			3.1 Exploration	
Section 3: Exploration and Drilling, Sampling Techniques and Data	3.1	(i)	Describe the data acquisition or exploration techniques and the nature, level of detail, and confidence in the geological data used (i.e. geological observations, remote sensing results, stratigraphy, lithology, structure, alteration, mineralisation, hydrology, geophysical, geochemical, petrography, mineralogy, geochronology, bulk density, potential deleterious or contaminating substances, geotechnical and rock characteristics, moisture content, bulk samples etc.). Confirm that data sets include all relevant metadata, such as unique sample number, sample mass, collection date, spatial location etc.	Data acquisition through diamond drilling and Borehole Electromagnetic (BHEM) survey. 12 500 m drilled at time of writing, in 21 holes (Appendix 2, Table 1): D zone: VDD24006, VDD24029, VDD24029B, VDD24029C, VDD24029D, VDD24055C, VDD24055D, VDD24055E, VDD24055F, VDD24055G, VDD24099(ongoing drilling) B zone, south: VDD0127B, VDD23019, VDD24036, VDD24115(ongoing drilling) B zone, central: VDD23116, VDD24057, VDD24113(ongoing drilling), VDD24118(ongoing drilling) ABBA (incl. A-zone): VDD24043B, VDD24043C

			<p>Three further drillholes (total 1140 m) in B zone are used for comparison: VDD21033, VDD22013, VDD23014</p> <p>Lithology, alteration, mineralization, structures logged from drill core. Limited geotechnical logging. BHEM used in ABBA zone to trace conductors, to estimate extent of new zone and plan future drilling. Bulk density measured, see section 3.7. Assaying was completed at ALS Geochemistry laboratory in Piteå.</p>
	(ii)	Identify and comment on the primary data elements (observation and measurements) used for the project and describe the management and verification of these data or the database. This should describe the following relevant processes: acquisition (capture or transfer), validation, integration, control, storage, retrieval and backup processes. It is assumed that data are stored digitally but hand-printed tables with well-organized data and information may also constitute a database.	Customized SQL database from M- Solutions called M-IDIS® Industry Data Integration System. Database download assay results directly from ALS's cloud-based database called Webtrieve (the accredited laboratory, see Section 3.4. i.). Database is backed up daily.
	(iii)	Acknowledge and appraise data from other parties and reference all data and information used from other sources.	References
	(iv)	Clearly distinguish between data / information from the property under discussion and that derived from surrounding properties	N/A
	(v)	Describe the survey methods, techniques and expected accuracies of data, including the methods for downhole surveying of drillholes. Specify the grid system used.	Gyro used for downhole surveying. Surveys completed by drilling contractors. SWEREF 99 2015
	(vi)	Discuss whether the data spacing, and distribution is sufficient to establish the degree of geological and grade continuity appropriate for the estimation procedure(s) and classifications applied.	Yes, spacing and distribution are sufficient.
	(vii)	Present representative models and / or maps and cross sections or other two- or three-dimensional illustrations of results, showing location of samples, accurate drill-hole collar positions, down-hole surveys, exploration pits, underground workings, relevant geological data, etc.	See Appendix 1
	(viii)	Report the relationships between mineralisation widths and intercept lengths are particularly important, the geometry of the mineralisation with respect to the drill hole angle. If it is not known and only the down-hole lengths are reported, confirm it with a clear statement to this effect (e.g. 'down-hole length, true width not known').	Down-hole lengths only, true width not known.
		3.2 Drilling Techniques	
3.2	(i)	Present the type of drilling undertaken (e.g. core, reverse circulation, open-hole hammer, rotary air blast, auger, Banka, sonic, etc.) and details (e.g. core diameter, triple or standard tube, depth of diamond tails, face-sampling bit or other type, whether core is oriented and if so, by what method, etc.).	The drilling is exclusively diamond core drilling. All cores are NQ size (47.6mm), except VDD24057 which has diameter 57.1mm. Core is oriented by drillers.

		(ii)	Describe whether core and chip samples have been geologically and geotechnically logged to a level of detail to support appropriate Mineral Resource estimation, technical studies, mining studies and metallurgical studies.	N/A
		(iii)	Describe whether logging is qualitative or quantitative in nature; indicate if core photography. (or costean, channel, etc.) was undertaken	Logging is qualitative. All cores are photographed wet and dry.
		(iv)	Present the total length and percentage of the relevant intersections logged.	12 500 meters of drillcore, 21 holes. Addt.l 1140 meters of drillcore, 3 holes, for comparison. See Appendix 2, Table 2 for assay results.
		(v)	Discuss the results of any downhole surveys of the drill holes.	BHEM conducted as part of exploration program.
			3.3 Sample method, collection, capture and storage	
Section 3: Exploration and Drilling, Sampling Techniques and Data	3.3	(i)	Describe the nature and quality of sampling (e.g. cut channels, random chips, or specific specialised industry standard measurement tools appropriate to the minerals under investigation, such as down hole gamma sondes, or handheld XRF instruments, etc.). These examples should not be taken as limiting the broad meaning of sampling.	Only drillhole pulp sampling has been used. Handheld XRF occasionally used to assist in preliminary estimation of Cu and Fe content or identifying minerals.
		(ii)	Describe the sampling processes, including sub-sampling stages to maximize representivity of samples. This should include whether sample sizes are appropriate to the grain size of the material being sampled. Indicate whether sample compositing has been applied.	See Section 3.4.iii
		(iii)	Appropriately describe each data set (e.g. geology, grade, density, quality, diamond breakage, geo-metallurgical characteristics etc.), sample type, sample-size selection and collection methods	For grade samples, see Section 3.4.iii For density samples, see Section 3.7. i and 3.7. iv
		(iv)	Report the geometry of the mineralisation with respect to the drill-hole angle. State whether the orientation of sampling achieves unbiased sampling of possible structures and the extent to which this is known, considering the Mineral deposit type. State if the intersection angle is not known and only the downhole lengths are reported.	Only down-hole lengths. A cutting line was occasionally drawn to create a more representative sample, for example where drill core runs parallel to a vein.
		(v)	Describe retention policy and storage of physical samples (e.g. core, sample reject, etc.)	Core stored in cold storage. Pulps stored in library. Rejects stored with lab or in own cold storage.
		(vi)	Describe the method of recording and assessing core and chip sample recoveries and results assessed, measures taken to maximise sample recovery and ensure representative nature of the samples and whether a relationship exists between sample recovery and grade and whether sample bias may have occurred due to preferential loss/gain of fine/coarse material.	TCR and RQD are measured for all cores. Drillers report core loss measured as core is drilled. Where core loss exceeded 0.3m sample intervals were not extended across missing interval. In grade calculations, results are diluted with 0 grade material where core could not be assayed.
		(vii)	If a drill-core sample is taken, state whether it was split or sawn and whether quarter, half or full core was submitted for analysis. If a non-core sample, state whether the sample was riffled, tube sampled, rotary split etc. and whether it was sampled wet or dry. the impact of water table or flow rates on recovery and introduction of sampling biases or contamination from above. Discuss the impact of variable hole diameters, e.g., by the use of a calliper tool.	Core was sawn, half-core analysed. Hole diameter was very consistent.

		(viii)	If a drill-core sample is taken, sufficient information should be supplied to assess the effects of core loss. Occasionally, only total core recovery is mentioned but at the same time the mineralized parts are designated as poor quality. This type of reporting is against the main principles of Transparency and Materiality. Heavy core losses throughout an ore body intersection can seriously undermine the confidence in a resource estimate. It is important to determine whether a relationship exists between grade and recovery (either positive or negative) to assess the potential for grade bias. In addition, it is important to state the method used to determine the core recovery: Total Core Recovery (TCR), Solid Core Recovery (SCR) and Rock Quality Designation (RQD).	TCR and RQD has been measured for all cores. In D zone ore, the rock quality is comparatively poor, with lower core recovery than in A and B zone. Where core loss is significant, grade calculations were diluted with 0 grade material across missing intervals. True grade is therefore likely to be higher than the calculated grades reported here.
			3.4 Sample Preparation and Analysis	
Section 3: Expl	3.4	(i)	Identify the laboratory(s) and state the accreditation status and Registration Number of the laboratory or provide a statement that the laboratories are not accredited. Record the steps taken by the Competent Person to ensure the results from a non-accredited laboratory are of an acceptable quality.	The accredited laboratory ALS Geochemistry, Piteå, performs the sample preparation. From there the pulps are sent for assay at other accredited ALS facilities.
		(ii)	Identify the analytical method. Discuss the nature, quality and appropriateness of the assaying and laboratory processes and procedures used and whether the technique is considered partial or total.	Multielement method ME-MS61 and Fire Assay method AA-Au21 have been utilised. They are considered to be appropriate for the mineralisation's at Viscaria.
		(iii)	Describe the process and method used for sample preparation, sub-sampling and size reduction, and likelihood of inadequate or non-representative samples (i.e. improper size reduction, contamination, screen sizes, granulometry, mass balance, etc.)	Drillholes with sample intervals marked by geologists were transported via courier to ALS, Piteå using chain of custody procedure. Diamond drill core was sawn longitudinally and split in half for sampling. Sample interval boundaries are marked on core boxes at the relevant position along the drill core. Sample preparation procedures are appropriate, with ALS preparing samples by crushing to < 2 mm, splitting using a riffle splitter, then pulverising to achieve a 250 g sample mass that is sub-sampled for analysis. Sample sizes have varied according to the length of core sample taken as determined by geological logging. Sample lengths are appropriate for the intersected mineralisation and minimum core diameters are greater than the maximum mineralisation crystal size. Pulverizing of crush materials are acceptable under the quality standard by ALS. ALS ships the sampled half-core, pulp and reject material separately to Viscaria Kiruna AB, where pulps are stored in a dry and warm place and the half-core is stored in three core storage facilities for later use and / or review. (Table 1 November 2022)
			3.5 Sampling Governance	

3.5	(i)	Discuss the governance of the sampling campaign and process, to ensure quality and representivity of samples and data, such as sample recovery, high grading, selective losses or contamination, core/hole diameter, internal and external QA/QC, and any other factors that may have resulted in or identified sample bias.	Average recovery was 98.5%, 98.7%, and 96.1% for B, ABBA zone incl. A zone, and D zone, respectively. They are monitored via systematic core measurements after each run. Systematic sampling was employed, with intervals chosen based on a predetermined grid to avoid selective sampling. Blanks and field duplicates were inserted. No significant contamination was detected during analysis. A rigorous QA/QC protocol was followed, including the insertion of blanks, standards, and duplicates at intervals. No sample bias was identified. Bias was controlled by ensuring full recovery across all mineralized intervals. All samples were handled according to a strict chain of custody, with samples stored in sealed containers before transport to the laboratory.
	(ii)	Describe the measures taken to ensure sample security and the Chain of Custody.	See Table 1 November 2022
	(iii)	Describe the validation procedures used to ensure the integrity of the data, e.g. transcription, input or other errors, between its initial collection and its future use for modelling (e.g. geology, grade, density, etc.)	Data integrity was ensured through a series of validation procedures. During data collection, field observations and survey measurements were cross-checked by the Viscaria geology team. Consistency and completeness checks were applied, with statistical outliers flagged for review through graphical and statistical methods. The data was reviewed through internal peer audits before being merged into the main database. Additional validation ensured that datasets were correctly formatted and compatible with the modelling software.
	(iv)	Describe the audit process and frequency (including dates of these audits) and disclose any material risks identified.	Regular audits performed by Viscaria geology team, most recent in 2022.
		3.6 Quality Control/Quality Assurance	
3.6	(i)	Demonstrate that adequate field sampling process verification techniques (QA/QC) have been applied, e.g. the level of duplicates, blanks, reference material standards, process audits, analysis, etc. If indirect methods of measurement were used (e.g. geophysical methods), these should be described, with attention given to the confidence of interpretation. Refer to measures taken to ensure sample representivity and the appropriate calibration of any measurement tools or systems used. QA/QC procedures used to check databases augmented with 'new' data have not resulted in corruption of previous versions containing stored 'old' data.	Duplicates, blanks and standards are inserted into sample programme at a frequency of minimum 1 duplicate/blank/standard per 10 samples.
	(ii)	Document the use of any independent check laboratory (umpire check samples). Identify the independent laboratory and details of its accreditation.	N/A
		3.7 Bulk Density	
3.7	(i)	Describe the method of bulk density determination with reference to the frequency of measurements, the size, nature and representativeness of the samples.	For the 21 exploration holes, a total of 2013 density measurements were taken (19/9/2024). Density measurements were made on whole core, with buoyancy method, before core is sent to the lab. Generally, density measurements were taken only in sampled intersections, with

				representative sections chosen for each lithology. In mineralized and ore zone intersections, measurements were taken in every sample interval. Core sections sampled were between 7 and 32 cm. Measured bulk density ranged from 2.11 to 4.89 g/cm ³ .
		(ii)	If target tonnage ranges are reported, state the preliminary estimates or basis of assumptions made for bulk density.	N/A
		(iii)	Discuss the representivity of bulk density samples of the material for which a grade range is reported.	N/A
		(iv)	Discuss the adequacy of the methods of bulk density determination for bulk material with special reference to accounting for void spaces (vugs, porosity etc.), moisture and differences between rock and alteration zones within the mineral deposit.	Porous and/or clay-rich rock is generally excluded as the measurement method used is not accurate for these. The lowest density measurements taken (2.1-2.6 g/cm ³) are likely due to porosity not visible to the geotechnician.
			3.8 Bulk-Sampling and/or Trial-mining	
	3.8	(i)	Indicate the location of individual samples (including map).	N/A
		(ii)	Describe the size of samples, spacing/density of samples recovered and whether sample sizes and distribution are appropriate to the grain size of the material being sampled.	N/A
		(iii)	Describe the method of mining and treatment.	N/A
		(iv)	Indicate the degree to which the samples are representative of the various types and styles of mineralisation and the mineral deposit as a whole.	N/A
	Section 4: Estimation and Reporting of Exploration Results, Mineral Resources and Mineral Reserves			
			4.1 Geological model and interpretation	
Section 4: Estimation and Reporting of Exploration Results, Mineral Resources and Mineral	4.1	(i)	Describe the geological model, construction technique and assumptions that forms the basis for the Exploration Results or Mineral Resource estimate. Discuss the sufficiency of data density to assure continuity of mineralisation and geology and provide an adequate basis for the estimation and classification procedures applied.	Published 2022 resource models, see www.viscaria.com A model of the mineralisation has been used as a reference to describe the exploration results (see appendix, Figure). The model is based on drillhole data but does not include the drillhole data from the exploration drilling and is therefore not a part of the publication of the exploration result.
		(ii)	Describe the nature, detail and reliability of geological information with which lithological, structural, mineralogical, alteration or other geological, geotechnical and geo-metallurgical characteristics were recorded.	Published 2022 resource models, see www.viscaria.com

	(iii)	Describe any obvious geological, mining, metallurgical, environmental, social, infrastructural, legal and economic factors that could have a significant effect on the prospects of any possible exploration target or mineral deposit.			Near-mine exploration, no factors specific to these findings.
	(iv)		Discuss all known geological data that could materially influence the estimated quantity and quality of the Mineral Resource.		N/A
	(v)		Discuss whether consideration was given to alternative interpretations or models and their possible effect (or potential risk) if any, on the Mineral Resource estimate.		N/A
	(vi)		Discuss geological discounts (e.g. magnitude, per reef, domain, etc.), applied in the model, whether applied to mineralized and / or un-mineralized material (e.g. potholes, faults, dykes, etc.).		N/A
		4.2 Estimation and modelling techniques			
4.2	(i)	Describe in detail the estimation techniques and assumptions used to determine the grade and tonnage ranges for any Exploration Targets, if reported in a Public Report.			N/A
	(ii)		Discuss the nature and appropriateness of the estimation technique(s) applied and key assumptions, including treatment of extreme grade values (cutting or capping), compositing (including by length and/or density), domaining, sample spacing, estimation unit size (block size), selective mining units, interpolation parameters and maximum distance of extrapolation from data points.		N/A
	(iii)		Describe assumptions and justification of correlations made between variables.		N/A
	(iv)		Provide details of any relevant specialized computer program (software) used, with the version number, together with the estimation parameters used.		N/A

		(v)		State the processes of checking and validation, the comparison of model information to sample data and use of reconciliation data, and whether the Mineral Resource estimate takes account of such information.	N/A
		(vi)		Describe the assumptions made regarding the estimation of any co-products, by-products or deleterious elements.	N/A
			4.3 Reasonable prospects for eventual economic extraction		
Section 4: Estimation and Reporting of Exploration Results, Mineral Resources and Mineral Reserves	4.3	(i)		Disclose and discuss the geological parameters. These would include (but not be limited to) volume / tonnage, grade and value / quality estimates, cut-off grades, strip ratios, upper- and lower- screen sizes.	N/A
		(ii)		Disclose and discuss the engineering parameters. These would include mining method, dilution, processing, geotechnical, geohydraulic and metallurgical) parameters.	N/A
		(iii)		Disclose and discuss the infrastructural including, but not limited to, power, water, site-access.	N/A
		(iv)		Disclose and discuss the legal, governmental, permitting, statutory parameters.	N/A
		(v)		Disclose and discuss the environmental and social (or community) parameters.	N/A
		(vi)		Disclose and discuss the marketing parameters.	N/A
		(vii)		Disclose and discuss the economic assumptions and parameters. These factors will include, but not limited to, commodity prices and potential capital and operating costs	N/A
		(viii)		Discuss any material risks	N/A
		(ix)		Discuss the parameters used to support the concept of "eventual"	N/A
				4.4 Classification Criteria	

	4.4	(i)		Describe criteria and methods used as the basis for the classification of the Mineral Resources into varying confidence categories.	N/A
			4.5 Reporting		
Section 4: Estimation and Reporting of Exploration Results, Mineral Resources and Mineral Reserves	4.5	(i)	Discuss the reported low and high-grades and widths together with their spatial location to avoid misleading the reporting of Exploration Results, Mineral Resources or Mineral Reserves.		Only exploration results are reported.
		(ii)	Discuss whether the reported grades in Exploration Targets are regional averages or if they are selected individual samples taken from the property under discussion.		Reported grades are individual samples from select drillholes.
		(iii)	State assumptions regarding mining methods, infrastructure, metallurgy, environmental and social parameters. State and discuss where no mining related assumptions have been made.		No mining related assumptions are made in the report.
		(iv)	State the specific quantities and grades / qualities which are being reported in ranges and/or widths, and explain the basis of the reporting		See Appendix 2, Table 2
		(v)		Present the detail for example open pit, underground, residue stockpile, remnants, tailings, and existing pillars or other sources in the Mineral Resource statement	N/A
		(vi)		Present a reconciliation with any previous Mineral Resource estimates. Where appropriate, report and comment on any historic trends (e.g. global bias).	N/A

		(vii)		Present the defined reference point for the tonnages and grades reported as Mineral Resources. State the reference point if the point is where the run of mine material is delivered to the processing plant. It is important that, in all situations where the reference point is different, such as for a saleable product, a clarifying statement is included to ensure that the reader is fully informed as to what is being reported.		N/A
		(viii)		If the CP is relying on a report, opinion, or statement of another expert who is not a CP, disclose the date, title, and author of the report, opinion, or statement, the qualifications of the other expert and why it is reasonable for the CP to rely on the other expert, any significant risks and any steps the CP took to verify the information provided.		N/A
		(ix)		State the basis of equivalent metal formulae, if applied.		Copper Equivalent (CuEq) assumes full recovery of copper and iron (68%). The calculations are based on Cu price USD 9,437 USD/t and Fe (68%) price 110 USD/t.
Section 5: Technical Studies						
			5.1 Introduction			
Section 5: Technical Studies	5.1	(i)	not applicable to Exploration Results	State the level of study – whether Scoping, Pre-Feasibility, Feasibility or ongoing Life of Mine	State the level of study – whether Pre-feasibility, Feasibility or ongoing Life of Mine. The Standard requires that a study to at least a Pre-Feasibility level has been undertaken to convert Mineral Resource to Mineral Reserve. Such studies will have been carried out and will include a mine plan or production schedule that is technically	N/A

				achievable and economically viable, and that all Modifying Factors have been considered.	
	(ii)			Provide a summary table of the Modifying Factors used to convert the Mineral Resource to Mineral Reserve for Pre-feasibility, Feasibility or on-going Life-of-Mine studies.	N/A
		5.2 Mining Design			
5.2	(i)	not applicable to Exploration Results	State assumptions regarding mining methods and parameters when estimating Mineral Resources or explain where no mining assumptions have been made.		N/A
	(ii)		Discuss Modifying factors taken into account in estimation of Mineral Resources	State and justify all modifying factors and assumptions made regarding mining methods, minimum mining dimensions (or pit shell) and internal and, if applicable, external) mining dilution and mining losses used for the techno-economic study and signed-	N/A

				off, such as mining method, mine design criteria, infrastructure, capacities, production schedule, mining efficiencies, grade control, geotechnical and hydrological considerations, closure plans, and personnel requirements.	
		(iii)		State what mineral resource models have been used in the study.	N/A
		(iv)		Explain the basis of (the adopted) cut-off grade(s) or quality parameters applied. Include metal equivalents if relevant	N/A
		(v)		Description and justification of mining method(s) to be used.	N/A
		(vi)		For open-pit mines, include a discussion of pit slopes, slope stability, and strip ratio.	N/A
		(vii)		For underground mines, discuss mining method, geotechnical considerations, mine design characteristics, and ventilation/cooling requirements.	N/A
Section 5: Technical Studies	5.2	(viii)	not applicable to Exploration Results	Discuss mining rate, equipment selected, grade control methods, geotechnical and	N/A

				hydrogeological considerations, health and safety of the workforce, staffing requirements, dilution, and recovery.	
	(ix)			State the optimisation methods and any software used in planning, list of constraints (practicality, plant, access, exposed Mineral Reserves, stripped Mineral Reserves, bottlenecks, draw control).	N/A
		5.3 Metallurgical and Test work			
5.3	(i)	not applicable to Exploration Results	Discuss the source of the sample, the representivity of the potential feed and the techniques used to obtain the samples, laboratory and metallurgical testing techniques.		N/A
	(ii)		Explain the basis for assumptions or predictions regarding metallurgical amenability and any preliminary mineralogical test work already carried out.		N/A
	(iii)		Discuss the possible processing methods and any processing factors that could have a material effect on the reasonable expectations of eventual economic extraction. Discuss the appropriateness of the processing methods to the style of mineralisation.	Describe and justify the processing method(s) to be used, equipment, plant capacity, efficiencies, and personnel requirements.	N/A

		(iv)		Discuss the nature, amount and representativeness of metallurgical test work undertaken and the recovery factors used. A detailed flow sheet / diagram and a mass balance should exist, especially for multi-product operations from which the saleable materials are priced for different chemical and physical characteristics.	N/A
		(v)		State what assumptions or allowances have been made for deleterious elements and the existence of any bulk-sample or pilot-scale test work and the degree to which such samples are representative of the ore body as a whole.	N/A
		(vi)		State whether the metallurgical process is well-tested technology or novel in nature. If novel, justify its use in Mineral Reserve estimation.	N/A
			5.4 Infrastructure		

5.4	(i)	not applicable to Exploration Results	Comment regarding the current state of infrastructure or the ease with which the infrastructure can be provided or accessed		N/A
	(ii)			Report in sufficient detail to demonstrate that the necessary facilities have been allowed for (which may include, but not be limited to, processing plant, tailings dam, leaching facilities, waste dumps, road, rail or port facilities, water and power supply, offices, housing, security, resource sterilisation testing etc.). Provide detailed maps showing locations of facilities.	N/A
	(iii)			Statement showing that all necessary logistics have been considered.	N/A
		5.5 Environmental, Social Performance, and Governance			

Section 5: Technical Studies	5.5	(i)	<p>General:</p> <ul style="list-style-type: none"> - Confirm that the company or reporting entity has addressed the host country environmental legal compliance requirements and any mandatory and/or voluntary standards or guidelines to which it subscribes - Identify the necessary permits that will be required and their status and where not yet obtained, confirm that there is a reasonable basis to believe that all permits required for the project will be obtained - Identify and discuss any sensitive areas that may affect the project as well as any other environmental factors including Interested and Affected Parties (I&AP) and/or studies that could have a material effect on the likelihood of eventual economic extraction. Discuss possible means of mitigation. - Identify any legislated social management programmes that may be required and discuss the content and status of these. - Outline and quantify the material socio-economic and cultural impacts that need to be mitigated, and their mitigation measures and where appropriate the associated costs. 	N/A
		(ii)	<p>Context: The project context is determined and described, including the following aspects:</p> <ul style="list-style-type: none"> • The locality’s physical geography, centres of population, economic and cultural characteristics; • Existing land and natural resource use for economic, cultural, recreational and conservation purposes (inclusive of environmental and cultural sites of interest); • Existing or historical industrial development and associated infrastructure including mining and quarrying in the region; and • Local governance structures and administrative bodies, their roles and responsibilities in relation to permitting and regulations. • Site access routes and any potential impact on environment or local communities • Provision of energy for activities (e.g. off-grid renewable energy, or sourced direct from local non-renewable power grid with plans for decarbonisation for future project if possible) 	See sections 1 and 2 for descriptions of locality. See www.viscaria.com and Tillståndsportal found on website for information on permitting, regulations and existing land use.

		(iii)	<ul style="list-style-type: none"> • High level assessment of level of water stress (e.g. potential for drought, flood and impact on water quality) • High level assessment of biodiversity (e.g. endangered species known in area) 	<ul style="list-style-type: none"> • Associated Environmental and seasonal constraint/ control/consent measures/modifying factors described • Identification of potential climate associated risks and impacts • Social economic and cultural constraint /control/consent measures/ modifying factors described • Any sensitive areas that may affect the project as well as any other environmental factors including I&AP and/or studies that could have a material effect on the likelihood of eventual economic extraction. • Management of project waste and anticipated requirements for large scale infrastructure for mine waste for future, including but not limited to waste dumps and tailings dams. 	See Viscaria's application for an environmental permit, found in Tillståndsportalen at www.viscaria.com .
	5.5	(iv)	Permits and permission: Identification of the necessary permits that will be required and their status, and where not yet obtained, and confirmation that there is a reasonable basis to believe that all permits required for the project will be obtained in a timely manner. Also include any records of penalties / fines or revoked permits complete with rationale.		All public documents relating to the permitting process can be found in Tillståndsportal at www.viscaria.com .
Section 5: Technical Studies		(v)	Liabilities: Describe any known rehabilitation activities, liability and / or compliance costs	<ul style="list-style-type: none"> • Describe the best cost estimate for closure inclusive of environmental, social material remaining liability and compliance costs. • Provide a description of mechanisms in place to address unplanned closure • If appropriate, describe bonding obligations in place to ensure that these liabilities can be funded on a qualitative and quantitative basis. 	All public documents relating to the permitting process can be found in Tillståndsportal at www.viscaria.com .
		(vi)	Description of stakeholder group characteristics Records of Community and Stakeholder relationships: Records kept of all engagements with all stakeholders from the outset of the project; A grievance and/or complaints procedure established, stakeholders' issues, concerns recorded and tracked until resolved.		All public documents relating to the permitting process can be found in Tillståndsportal at www.viscaria.com .
		(vii)		A data management system implemented to record and track engagements; Provisions made for vulnerable and or underrepresented stakeholder groups Presence, or not of Indigenous People, if FPIC triggered, how is this managed	N/A

	(viii)	Health and safety protocols and procedures required for exploration target definition inclusive of evidence of adherence to them and ongoing health and safety record.	Health and safety procedures and protocols, including community safety and security, across the exploration programme inclusive of evidence of adherence to them and ongoing health and safety record	Gruvaktiebolaget Viscaria have health and safety protocols and use the GRIA reporting system for systematic work. The company Viscaria has standard contracts quality assured by lawyers, as well as associated basic requirements and a supplier handbook to meet requirements regarding corruption, bribery and other irregularities, as well as to ensure "good suppliers" at Viscaria.
	(ix)	Opportunities for contributing to the local economy identified and utilized where appropriate.	Legislated and or voluntary social development programmes that may be required and content and status of these.	The company is the initiator of the association Kiruna Växer, which is an association that will be involved in developing Kiruna. In addition to Viscaria, participants are also LKAB, Sparbanken Nord, LTH and Kiruna Municipality. The association has participated in Housing and Employer Conferences, the centre of the Luossavaara adventure and several annual festivals to promote the municipality's growth.
	(x)		Material socio-economic and cultural impacts that need to be managed, and where appropriate the associated costs.	N/A
	(xi)	Description of corporate governance board structure: gender, nationality, tenure, roles, responsibilities and process for selection of Board members, and Board remuneration processes and procedures		See www.viscaria.com Gruvaktiebolaget Viscaria is a listed company on Nasdaq and follows the requirements and policies that are a requirement to be on the stock exchange. The company recently was awarded in AllBrights Green List (gender equality in leadership).
	(xii)	<ul style="list-style-type: none"> • Commitment to GIIP: transparency, diversity, commitment to ESG described • Corporate commitment to social performance described/ provided • Corporate commitment to environmental stewardship described / provided 	<ul style="list-style-type: none"> • Description of how corporate compliance is assured and verified • Demonstrable commitment to GIIP: transparency, diversity, commitment to ESG described • Demonstrable commitment to social performance described • Demonstrable commitment to environmental stewardship described 	All public documents relating to the permitting process can be found in Tillståndsportalen at www.viscaria.com .
	(xiii)	Integrated Risk Management: Description of identified potential modifying factors and management actions taken to manage them where appropriate	<ul style="list-style-type: none"> • Description of proposed mitigation plans for identified modifying factors and management actions taken to manage them where appropriate. • Description of any additional risks that may impact on the long term future of the project, even if not deemed to be material at the current time. • Description of how the risk assessment process outlined here is integrated with the overall risk management framework for the company as a whole. 	www.viscaria.com

			5.6 Market Studies and Economic Criteria				
Section 5: Technical Studies	5.6	(i)	not applicable to Exploration Results	Discuss any technical and economic factors likely to influence the prospect of economic extraction.	Describe the valuable and potentially valuable product(s) including suitability of products, co-products and by products to market.	N/A	
		(ii)				Describe product to be sold, customer specifications, testing, and acceptance requirements. Discuss whether there exists a ready market for the product and whether contracts for the sale of the product are in place or expected to be readily obtained. Present price and volume forecasts and the basis for the forecast.	N/A
		(iii)				State and describe all economic criteria that have been used for the study such as capital and operating costs, exchange rates, revenue / price curves, royalties, cut-off grades, reserve pay limits.	N/A

		(iv)		Summary description, source and confidence of method used to estimate the commodity price/value profiles used for cut-off grade calculation, economic analysis and project valuation, including applicable taxes, inflation indices, discount rate and exchange rates.	N/A
		(v)		Present the details of the point of reference for the tonnages and grades reported as Mineral Reserves (e.g. material delivered to the processing facility or saleable product(s)). It is important that, in any situation where the reference point is different, a clarifying statement is included to ensure that the reader is fully informed as to what is being reported.	N/A
		(vi)		Justify assumptions made concerning production cost including transportation, treatment, penalties,	N/A

					exchange rates, marketing and other costs. Provide details of allowances that are made for the content of deleterious elements and the cost of penalties.	
		(vii)			Provide details of allowances made for royalties payable, both to Government and private.	N/A
		(viii)			State ownership, type, extent and condition of plant and equipment that is significant to the existing operation(s).	N/A
		(ix)			Provide details of all environmental, social and labour costs considered	N/A
			5.7 Risk Analysis			
Section 5: Technical Studies	5.7	(i)	A high-level assessment should be made of key areas of uncertainty which may affect exploration outcomes. An assessment should be provided on the chances of exploration success, together with consideration of any potential threats, such as ESG aspects, which could hinder eventual development of a mining or extraction project in the exploration area.”	Report an assessment of technical, environmental, social, economic, political and other key risks to the project. Describe actions that will be taken to mitigate and/or manage the identified risks.		Near-mine exploration, mostly within existing exploitation concessions – Main risk is not enough/sufficient data for declaring future exploration targets and mineral resources. Risks with increasing depth of the deposit requires higher mining costs as well as better understanding of rock mass characterization, in situ stress, higher temperature and water pressure etc. However, the exploration results fall within the current analysis for mining operation, due to its closeness to declared mineral resources.
			5.8 Economic Analysis			

	5.8	(i)	not applicable to Exploration Results	Describe the basis on which reasonable prospects for eventual economic extraction has been determined, including any material assumptions made in determining the 'reasonable prospects for eventual economic extraction'.	State and justify the inclusion of any Inferred Resources in the Pre-feasibility and Feasibility Studies economic analysis. Report the sensitivity to the inclusion of any Inferred Resources.	N/A
		(ii)		At the relevant level (Scoping Study, Pre-feasibility, Feasibility or on-going Life-of Mine), provide an economic analysis for the project that includes:		N/A
		(iii)		Cash Flow forecast on an annual basis using Mineral Reserves or an annual production schedule for the life of the project		N/A
		(iv)		A discussion of net present value (NPV), internal rate of return (IRR) and payback period of capital		N/A
		(v)		Sensitivity or other analysis using variants in commodity price, grade, capital and operating costs, or other significant parameters, as appropriate and discuss the impact of the results.		N/A
Section 6: Estimation and Reporting of Mineral Reserves						
6.1 Estimation and Modelling Techniques						
Section 6: Estimation and Reporting of Mineral Reserves	6.1	(i)	not applicable to Exploration Results	Describe the Mineral Resource estimate used as a basis for the conversion to a Mineral Reserve.		N/A
		(ii)		Report the Mineral Reserve Statement with sufficient detail indicating if the mining is open pit or underground plus the source and type of mineralisation, domain or ore body, surface dumps, stockpiles and all other sources.		N/A

		(iii)		<p>If Inferred resources are used in assessing Mineral reserves, then report and discuss a comparison between the two possibilities, the one with inclusion of Inferred Mineral Resources and the one without inclusion, in such a way so as not to mislead the investors.</p> <p>Identify the quantity of the Inferred Mineral Resources included and the sensitivity of the inclusion to the study.</p>	N/A
		(iv)		<p>A Mineral Reserve Statement in sufficient detail indicating if the mining is open pit or underground plus the source and type of mineralisation, domain or ore body, surface dumps, stockpiles and all other sources.</p>	N/A
		(v)		<p>Provide a reconciliation reporting historic reliability of the performance parameters, assumptions and modifying factors</p>	N/A

					including a comparison with the previous Reserve quantity and qualities, if available. Where appropriate, report and comment on any historic trends (e.g. global bias)	
			6.2 Classification Criteria			
	6.2	(i)			Describe and justify criteria and methods used as the basis for the classification of the Mineral Reserves into varying confidence categories, based on the Mineral Resource category, and including consideration of the confidence in all the modifying factors.	N/A
			6.3 Reporting			
Section 6: Estimation and Reporting of Mineral Reserves	6.3	(i)			Discuss the proportion of Probable Mineral Reserves, which have been derived from Measured Mineral Resources (if any), including the reason(s) therefore.	N/A
		(ii)			Present details of for example open pit, underground, residue stockpile, remnants, tailings,	N/A

				and existing pillars or other sources in respect of the Mineral Reserve statement	
		(iii)		Present the details of the defined reference point for the Mineral Reserves. State where the reference point is the point where the run of mine material is delivered to the processing plant. It is important that, in all situations where the reference point is different, such as for a saleable product, a clarifying statement is included to ensure that the reader is fully informed as to what is being reported. State clearly whether the tonnages and grades reported for Mineral Reserves are in respect of material delivered to the plant or after recovery.	N/A
		(iv)		Present a reconciliation with the previous Mineral Reserve estimates. Where appropriate, report and comment	N/A

				on any historic trends (e.g. global bias).	
		(v)		Confirm that only Measured and Indicated Mineral Resources can be considered for inclusion in the Mineral Reserve.	N/A
		(vi)		State whether the Measured Mineral Resources and Indicated Mineral Resources are inclusive of or additional to the Mineral Reserves.	N/A
		6.4 Specific for Metal Equivalents or Combined Grades Reporting			
	6.4	(i)	Confirm that all reports comply with section 9 (paragraphs 9.1 to 9.5) of the PERC Reporting Standard.		
		(ii)		Discuss and describe the basis for the grade estimation for each metal relating to the metal equivalence or combined grade	N/A
		(iii)		Disclose all economic criteria that have been used for the calculation such as exchange rates, revenue / price curves, royalties, cut-off grades, pay limits.	N/A
		(iv)		Discuss the basis for assumptions or predictions regarding metallurgical factors such as recovery used in the metal equivalents or combined grades calculation.	N/A
		(v)		Show the calculation formula used.	N/A
Section 7: Audits and Reviews					
		7.1 Audits and Reviews			
Section 7: Audits and Reviews	7.1	(i)	State type of review/audit (e.g. independent, external), area (e.g. laboratory, drilling, data, environmental compliance etc.), date and name of the reviewer(s) together with their recognized professional qualifications. State the level of review/audit (desk-top, on-site comparison with standard procedures, or endorsement where auditor/reviewer has checked the work to the extent they stand behind it as if it were their own work).		See earlier sections.

		(ii)	Disclose the conclusions of relevant audits or reviews. Note where significant deficiencies and remedial actions are required.		N/A
Section 8: Other Relevant Information					
			8.1 Other Relevant Information		
Section 8: Other Relevant Information	8.1	(i)	Discuss all other relevant and material information not discussed elsewhere.		N/A
Section 9: Qualification of Competent Person(s) and other key technical staff. Date and Signature Page					
			9.1 Competent Person Details		
Section 9: Competent Person Signoff	9.1	(i)	State the full name, registration number and name of the professional body or RPO, for all the Competent Person(s). State the relevant experience of the Competent Person(s) and other key technical staff who prepared and are responsible for the Public Report.		See Competent Persons Certificate
		(ii)	State the Competent Person's relationship to the issuer of the report.		See Competent Persons Certificate
		(iii)	Provide the Certificate of the Competent Person, including the date of sign-off and the effective date, in the Public Report.		See Competent Persons Certificate

Appendix 1 – Figures

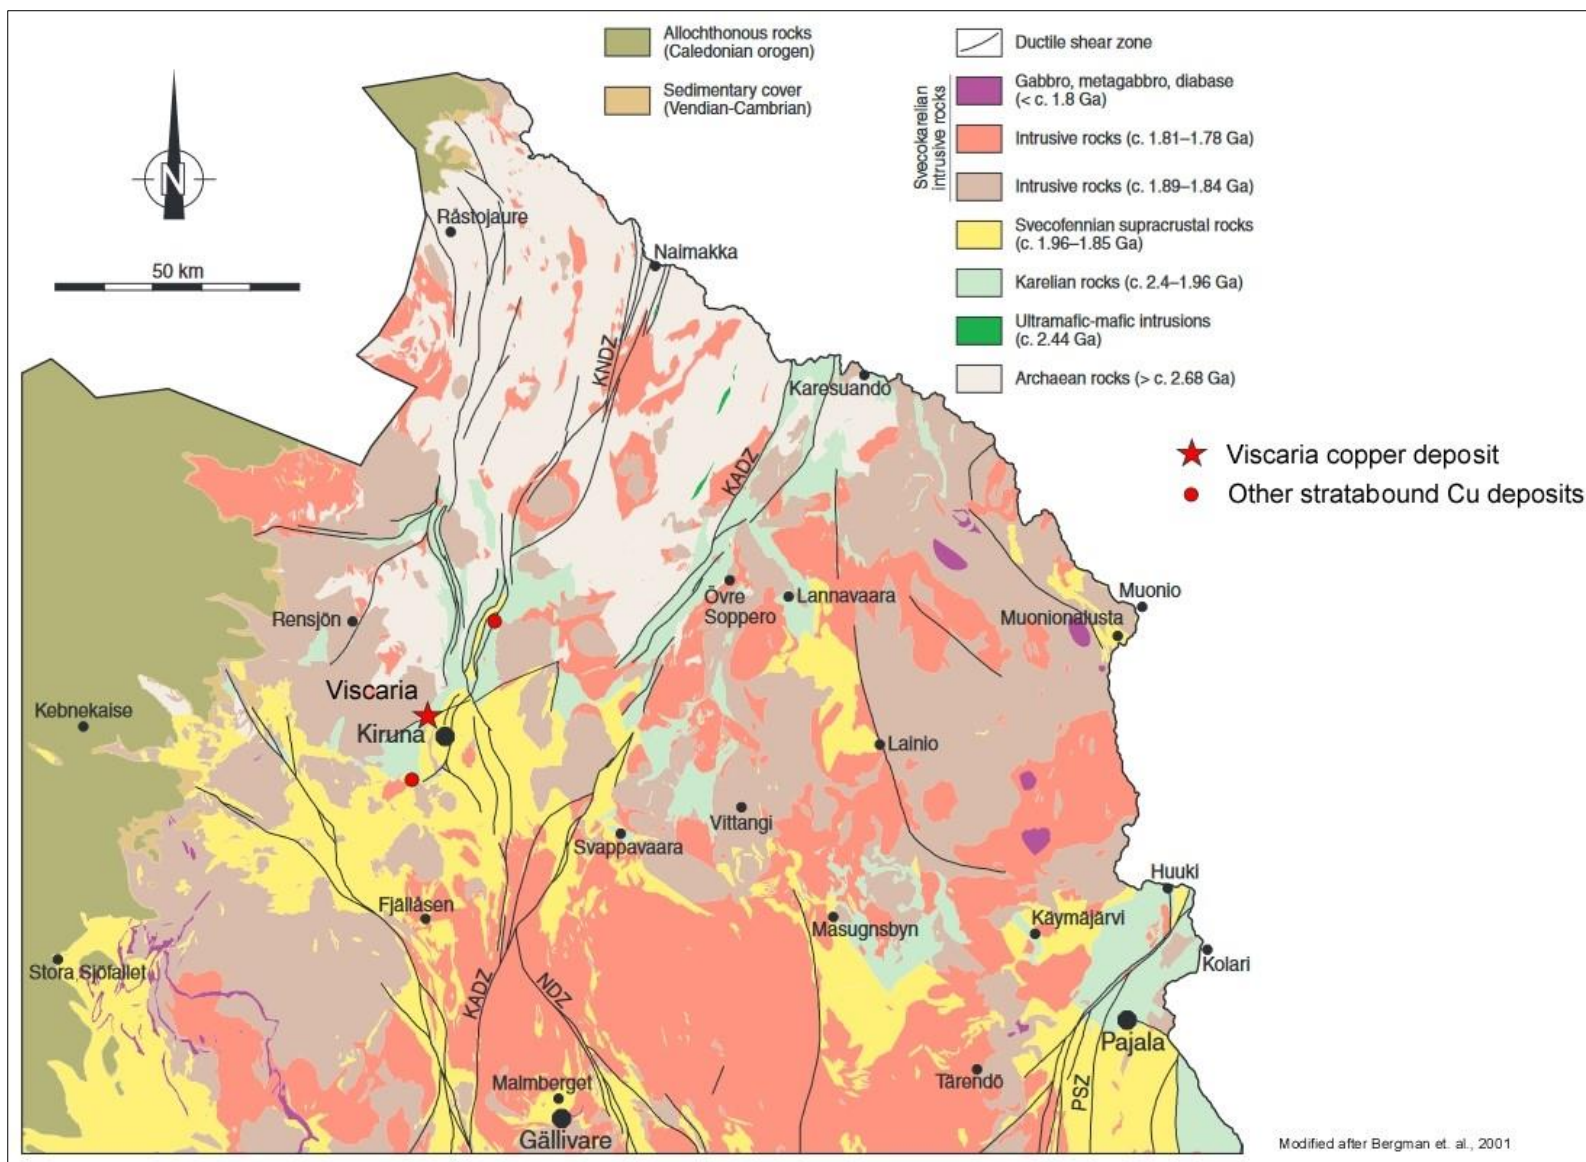


Figure 1. Geological structural map of Norrbotten showing the location of the Viscaria deposit. Modified after Berman et al 2001.

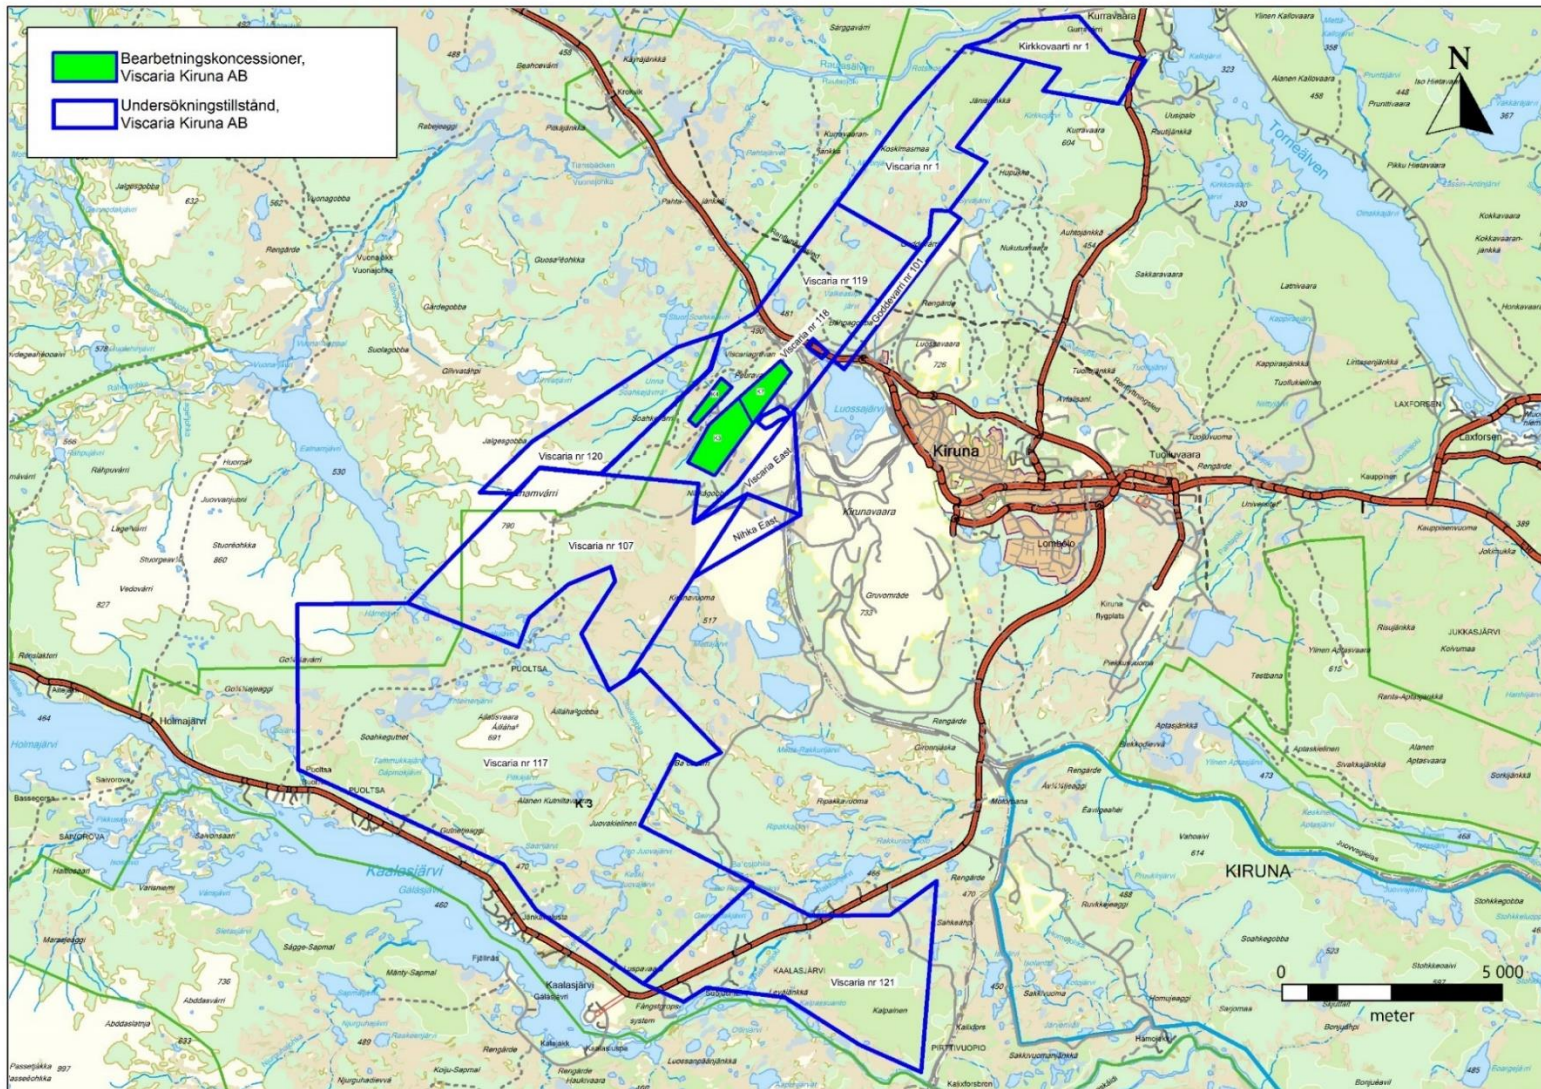


Figure 2. Overview map of Viscaria Kiruna AB's tenures effective date 20240912. Exploitation concessions (bearbetningskoncessioner) marked in green and Exploration permits (undersökningstillstånd) outlined in blue.



Figure 3. Satellite map of Viscaria area showing drillhole traces declared in the exploration results relative to mineralized zones (orange).

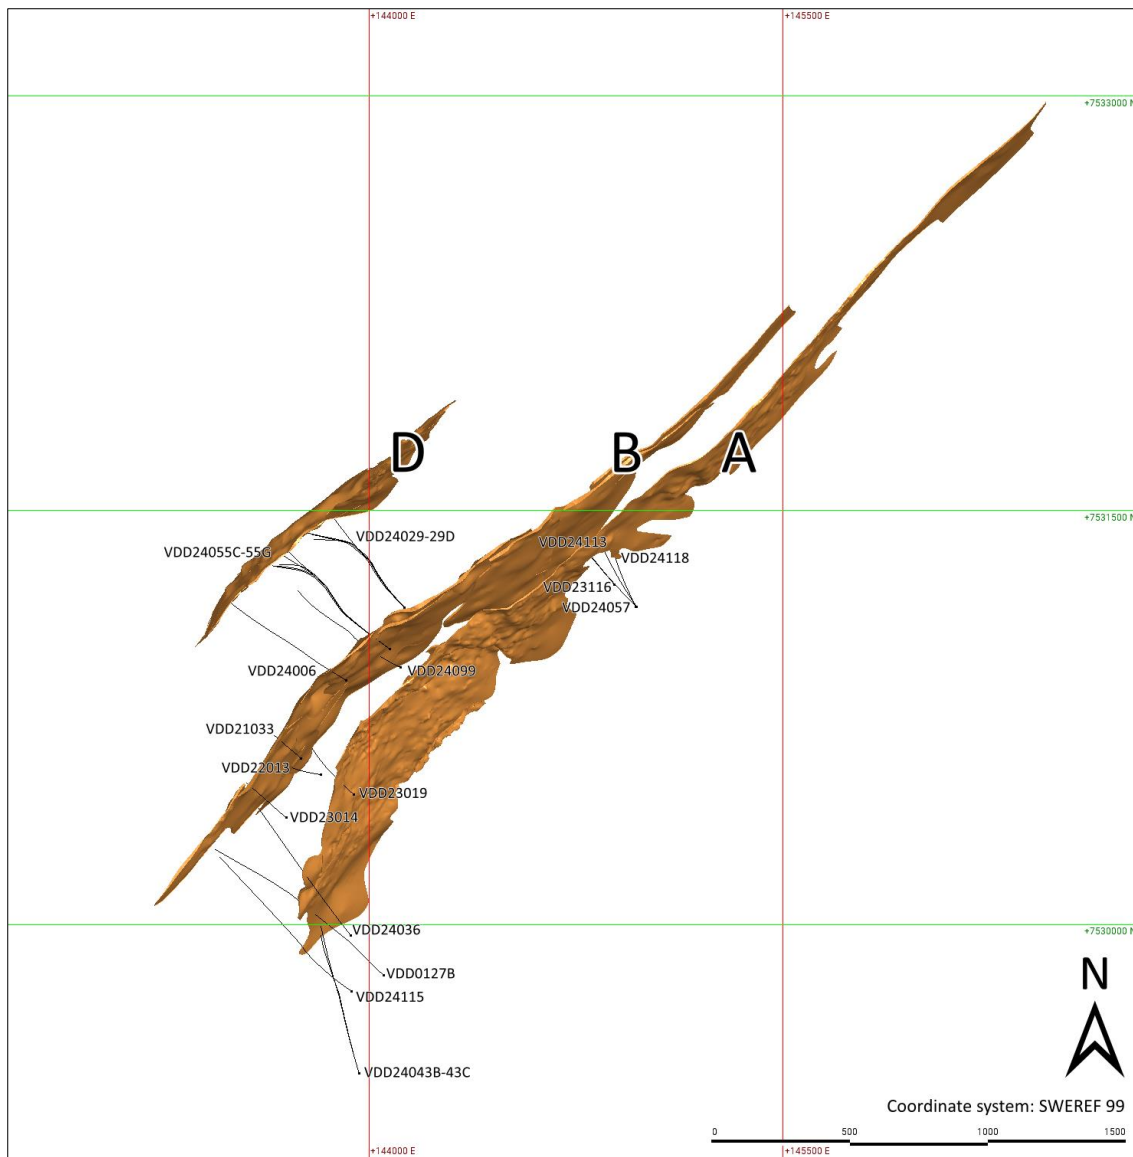


Figure 4. Top view showing drillhole IDs and traces in relation to models of the mineralized zones in Viscaria.

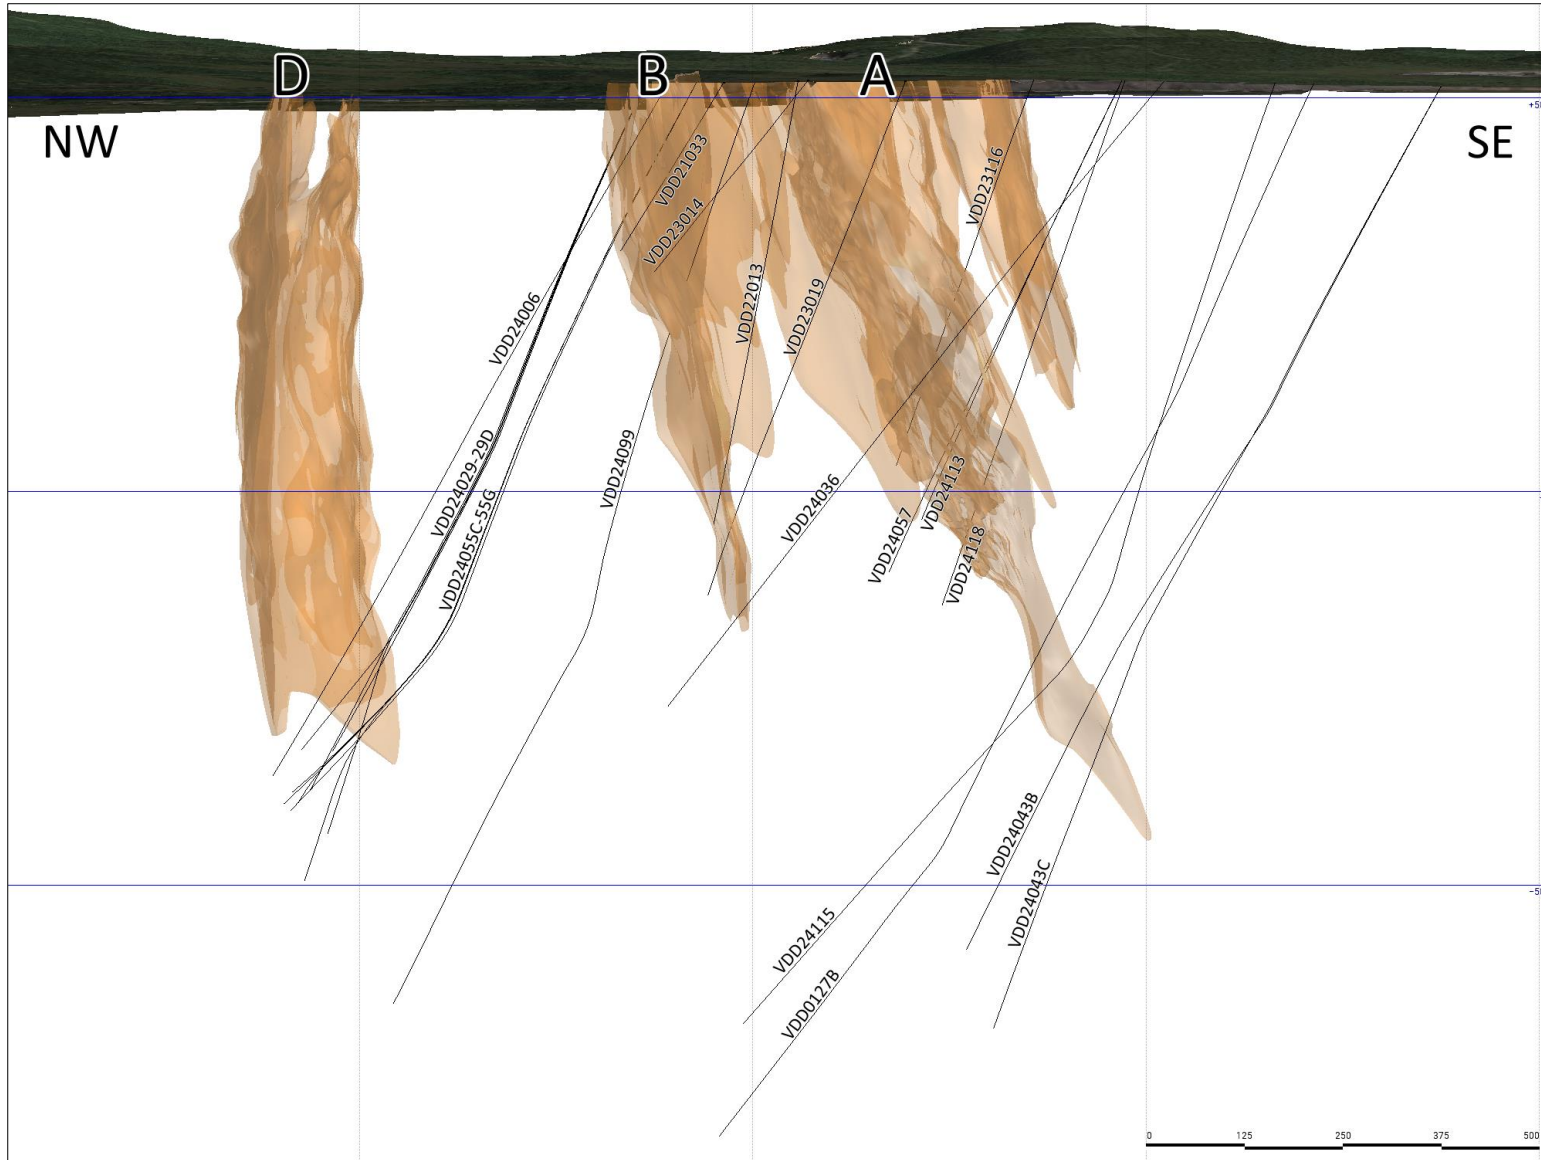


Figure 5: Side view showing orebodies A, B, D with drillhole traces. Facing NE.

Appendix 2 – Tables

Table 1. Collar table of drillholes

The following table shows the collar location, core size and target zone for each drillhole.

HOLE_ID	MAXIMUM DEPTH (m)	EASTING	NORTHING	ELEVATION	CORE SIZE	ZONE
VDD0127B	1557.7	144052.99	7529815.83	530.93	NQ	ABBA, B
VDD21033	251.9	143752.90	7530602.45	523.30	NQ	B
VDD22013	576.4	143826.49	7530542.98	524.70	NQ	B
VDD23014	312.8	143699.86	7530386.37	526.53	NQ	B
VDD23019	701.6	143945.54	7530470.44	525.02	NQ	B
VDD23116	566.6	144888.95	7531231.26	564.63	NQ	B
VDD24006	1016.5	143916.66	7530885.02	521.25	NQ	D
VDD24029	953.2	144128.58	7531148.77	529.78	NQ	D
VDD24029B	986.3	144128.58	7531148.77	529.78	NQ	D
VDD24029C	1061	144128.58	7531148.77	529.79	NQ	D
VDD24029D	1017	144128.58	7531148.77	529.78	NQ	D
VDD24036	1037.1	143934.14	7529959.75	536.24	NQ	B
VDD24043B	1356.2	143963.10	7529461.40	548.70	NQ	A, ABBA
VDD24043C	1426.2	143963.10	7529461.40	548.70	NQ	A, ABBA
VDD24055C	1079.2	144074.62	7530997.78	528.26	NQ	D
VDD24055D	1073.9	144074.62	7530997.78	528.26	NQ	D
VDD24055E	1078.3	144074.62	7530997.78	528.26	NQ	D
VDD24055F	1080.7	144074.62	7530997.78	528.26	NQ	D
VDD24055G	1153.8	144074.62	7530997.78	528.26	NQ	D
VDD24057	728.65	144967.40	7531151.06	553.21	WL-76	B
VDD24099 (ongoing)	902.2	144113.55	7530930.09	532.33	NQ	D
VDD24113 (ongoing)	655.5	144967.13	7531151.40	552.59	NQ	B
VDD24115 (ongoing)	1419	143935.40	7529758.70	537.80	NQ	A, ABBA
VDD24118 (ongoing)	750	144967.13	7531151.40	552.59	NQ	B

Table 2. Assay results

The following table shows assay results for the exploration drillholes. First section summarizes the results while section two provides a full description of assay results. For VDD24099, VDD24113, VDD24115 and VDD24118 assay results are not yet available.

Section 1: Summary

Ore grades are weighted by density and length with the formula: $\Sigma(\text{length} \times \text{grade} \times \text{density}) / \Sigma(\text{length} \times \text{density})$.

Where there is core loss within the intersection, the intersection is diluted with 0 grade material. In VDD24055C core loss within the ore intersection is 3m over a total length of 33.92m, with 2.69m of core loss occurring in the high-grade section between 1057.3m and 1064.5. Grade values for VDD24055C are thus heavily diluted. No other drillhole has more than 1m of core loss within the ore intersection.

In infill drillholes density measurements were made in every assay interval. In exploration drillholes measurements were made for every rock type. For assay intervals where no measurement was made, average density for the rock type was used for the grade weight. In the D zone the variation in density is high (2.6-4.6 g/m³) over short distances, so average density values can have higher uncertainty. However, the D zone drillholes reported have density measurements for most assay intervals, so average density is believed to be accurate.

VDD24043B has few density measurements in the A-zone intersection, while VDD24043C has few in the A-zone and ABBA intersections. Density variation in these areas is relatively small (2.7-3.3 g/m³) and there are enough density measurements for each rock type to give reliable averages.

D zone						
Hole ID	Depth from	Depth to	Sample length (m)	Cu (%)	Fe (%)	S (%)
VDD24029	919.55	951.6	32.05	0.23	7.69	0.70
	937.14	939.25	2.11	1.09	31.74	1.36
VDD24029B	950.32	985.5	35.18	0.26	20.97	0.65
	967.76	985.5	17.74	0.49	19.90	1.09
	975.51	980.04	4.53	1.04	23.70	1.92
VDD24029C	1025.1	1054.16	29.06	0.51	17.05	1.18
	1047.4	1053.04	5.64	1.33	47.24	2.51
VDD24029D	989.43	1011.05	21.62	0.54	30.09	1.62
	990.2	996.66	6.46	1.00	47.01	2.77
VDD24055C	1034.16	1068.08	33.92	0.54	21.09	0.68
	1057.3	1064.5	7.2	1.41	25.63	1.53
VDD24055D	1046.74	1072.35	25.61	0.57	26.28	0.69
	1057.93	1061.56	3.63	2.18	47.20	2.25
VDD24055E	1052.4	1078.3	25.9	0.40	25.25	0.70
	1064.53	1070.43	5.9	1.27	27.37	1.45
VDD24055F	1040.75	1067.15	26.4	0.52	25.24	0.86
	1049.6	1054.72	5.12	0.97	32.48	1.52

VDD24055G	1107	1150.2	43.2	1.12	31.35	1.28
	1112.9	1116.2	3.3	2.65	44.27	2.97
	1122.12	1125.68	3.56	2.38	42.63	2.71
	1129.88	1134.02	4.14	1.67	35.27	1.70
VDD24006	968.15	1007.9	39.75	0.08	13.42	0.33
	992.44	997	4.56	0.27	25.99	0.44

Zone	Hole ID	Depth from	Depth to	Sample length (m)	Cu (%)	Fe (%)	Ag (g/t)
B zone	VDD0127B incl.	1236.06	1347.8	111.74	0.54	10.40	0.61
		1239.62	1249.92	10.3	1.00	11.86	0.93
		1309.02	1323.5	14.48	1.40	9.08	1.56
		1333.12	1347.8	14.68	0.63	4.76	1.03
	VDD23116 incl.	434.25	566.6	132.35	0.35	14.24	0.72
		496.85	556	59.15	0.70	14.93	1.42
		498.1	511.43	13.33	2.42	19.06	4.96
	VDD23019 incl.	619.1	701.6	82.5	0.39	11.57	1.28
		633.69	665.1	31.41	0.82	14.47	2.61
		639.76	651.6	11.84	1.23	14.86	3.66
	VDD24036 incl.	929.6	1037.1	107.5	0.07	14.16	0.16
		951.7	1003.82	52.12	0.11	15.60	0.26
		952.71	964.94	12.23	0.24	21.66	0.47
	VDD24057 incl.	555.36	585.53	30.17	0.41	16.59	0.69
		560.72	563.11	2.39	1.13	15.96	1.34
		580.17	584.52	4.35	1.08	21.51	2.54
	VDD21033	174.2	191.9	17.7	0.98	15.47	2.02
VDD23014	270.3	286.35	16.05	0.77	14.11	2.14	
VDD22013 incl.	503.6	566.35	62.75	1.12	23.99	3.27	
	542.15	556.3	14.15	2.55	34.36	7.44	
ABBA	VDD0127B	964.25	1051.08	86.83	0.42	15.04	0.92
		988.15	998.8	10.65	1.36	21.01	2.71
		1048.8	1051.08	2.28	3.66	23.42	10.36
	VDD24043B	1167.6	1260.7	93.1	0.40	16.72	0.87
		1198.2	1218.75	20.55	0.92	18.85	1.82
		1248.35	1260.7	12.35	0.68	16.93	2.13
	VDD24043C	1153.05	1302	148.95	0.28	14.48	0.63
		1226.05	1246.6	20.55	0.64	17.91	1.46
		1236.25	1244.5	8.15	1.02	18.29	2.42
		1285.25	1293	7.75	0.62	14.33	1.39
	A zone	VDD24043B	916.6	1052.1	135.5	0.13	10.51

	923	986.65	63.65	0.22	10.06	0.33
	982.05	986.2	4.15	1.80	15.88	2.46
VDD24043C	1000.35	1071.5	71.15	0.21	11.59	0.45
	1004.4	1009.65	5.25	0.62	14.23	1.15

Unassayed drillcores

VDD24099 (D zone) intersects 40 m of Cu-mineralized rock, drilling still ongoing, assays pending.

VDD24113 (B zone) intersects 50 m of Cu-mineralized rock, assays pending.

VDD24115 (ABBA) intersects 350 m of Cu-mineralized rock, assays pending.

VDD24118 (B zone) is not yet logged.

CuEq% for select D zone intervals

Copper Equivalent (CuEq%) assumes full recovery of copper and iron (68%). The calculations are based on Cu USD 9,437 USD/t; Fe (68%) 110 USD/t.

Hole ID	From	To	interval	Cu (%)	Fe (%)	CuEq (%)
VDD24029C	1025.1	1054.16	29.06	0.51	17.05	0.64
	1047.4	1053.04	5.64	1.33	47.24	1.70
VDD24055C	1034.16	1068.08	33.92	0.55	21.09	0.72
	1057.3	1064.5	7.2	1.41	25.63	1.62
VDD24055G	1107	1150.2	43.2	1.12	31.35	1.37
	1112.9	1116.2	3.3	2.65	44.27	3.00
	1122.12	1125.68	3.56	2.38	42.63	2.72
	1129.88	1134.02	4.14	1.67	35.27	1.95

Section 2 – Assay results

Density measurements that are average values, not real measurements, are marked blue.

Core loss intervals are marked red. All core loss intervals are given an average density value.

D zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	S (%)	Density (g/cm³)
VDD24006	968.15	970.82	2.67	VS047304	0.20	10.90	0.27	2.95
	970.82	973.56	2.74	VS047305	0.13	11.30	0.56	2.93
	973.56	975.32	1.76	VS047306	0.01	11.20	0.04	3
	975.32	977.7	2.38	VS047307	0.00	6.10	0.11	2.8
	977.7	979.75	2.05	VS047308	0.00	10.85	0.38	2.94
	979.75	981.8	2.05	VS047309	0.00	10.10	0.38	2.91
	981.8	984.41	2.61	VS047310	0.01	5.85	0.10	2.87
	984.41	987.02	2.61	VS047311	0.02	3.57	0.08	2.7
	987.02	988.32	1.3	VS047312	0.00	4.25	0.38	2.77
	988.32	989.62	1.3	VS047314	0.02	3.97	0.42	2.78
	989.62	991.03	1.41	VS047315	0.08	4.60	0.31	2.87
	991.03	992.44	1.41	VS047316	0.03	4.68	0.53	2.78
	992.44	993.1	0.66	VS047317	1.29	9.41	1.83	2.95
	993.1	993.76	0.66	VS047318	0.17	6.48	0.52	2.92
	993.76	994.42	0.66	VS047319	0.16	7.14	0.62	2.83
	994.42	995.67	1.25	VS047321	0.11	36.20	0.13	3.88
	995.67	997	1.33	VS047323	0.12	37.00	0.10	3.79
	997	998.5	1.5	VS047324	0.03	17.70	0.03	3.07
	998.5	1000.2	1.7	VS047325	0.01	30.20	0.03	4.22
	1000.2	1001.3	1.1	VS047326	0.00	7.38	0.01	2.85
1001.3	1003.2	1.9	VS047327	0.00	10.50	0.02	2.82	
1003.2	1004.6	1.4	VS047328	0.29	21.60	1.12	2.8	
1004.6	1006.1	1.5	VS047329	0.05	15.40	0.96	2.8	
1006.1	1007.9	1.8	VS047330	0.04	24.00	0.70	2.8	
VDD24029	919.55	920.67	1.12	VS047516	0.65	4.83	1.28	2.73
	920.67	921.82	1.15	VS047517	0.12	4.65	0.24	2.82
	921.82	922.89	1.07	VS047519	0.01	2.68	0.19	2.69
	922.89	923.96	1.07	VS047520	0.01	2.73	0.21	2.65
	923.96	925.03	1.07	VS047521	0.00	3.01	0.15	2.76
	925.03	926.05	1.02	VS047523	0.17	4.24	0.55	2.76

D zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	S (%)	Density (g/cm ³)
	926.05	927.07	1.02	VS047524	0.03	3.59	0.20	2.67
	927.07	928.14	1.07	VS047525	0.10	4.88	1.56	2.68
	928.14	929.22	1.08	VS047526	0.04	4.81	1.70	2.78
	929.22	930.35	1.13	VS047527	0.75	5.41	1.88	2.78
	930.35	931.38	1.03	VS047528	0.04	8.88	0.06	2.95
	931.38	932.44	1.06	VS047530	0.00	2.85	0.02	2.85
	932.44	933.5	1.06	VS047531	0.00	2.49	0.01	2.66
	933.5	934.45	0.95	VS047532	0.00	6.09	0.02	2.81
	934.45	935.8	1.35	VS047533	0.13	1.59	0.16	2.75
	935.8	937.14	1.34	VS047534	0.33	4.90	0.73	2.76
	937.14	938.33	1.19	VS047536	0.69	21.30	1.00	3.06
	938.33	939.25	0.92	VS047537	1.50	42.30	1.72	3.91
	939.25	940.35	1.1	VS047539	0.23	20.50	1.02	2.88
	940.35	941.46	1.11	VS047540	0.03	10.80	1.32	2.93
	941.46	942.19	0.73	VS047541	0.06	14.95	1.93	3.25
	942.19	942.98	0.79	VS047542	0.08	16.10	0.62	3.19
	942.98	944.28	1.3	VS047544	0.01	1.85	0.09	2.78
	944.28	945.58	1.3	VS047545	0.09	2.16	0.46	2.73
	945.58	946.88	1.3	VS047546	0.01	2.27	0.05	2.77
	946.88	948.18	1.3	VS047547	0.01	0.58	0.03	2.73
	948.18	949.48	1.3	VS047548	0.13	1.92	1.34	2.78
	949.48	950.59	1.11	VS047549	0.08	1.02	0.31	2.74
	950.59	951.6	1.01	VS047551	1.06	17.80	1.53	3.12
	950.32	952.6	2.28	VS048244	0.00	5.23	0.02	2.75
	952.6	953	0.4	CORELOSS	0.00	0.00	0.00	2.8
	953	953.48	0.48	VS048245	0.23	11.25	2.99	3.09
	953.48	954.54	1.06	VS048246	0.01	16.30	0.29	3.26
	954.54	955.64	1.1	VS048247	0.07	2.75	0.71	2.73
	955.64	956.96	1.32	VS048249	0.05	23.20	0.12	3.16
VDD24029B	956.96	958.3	1.34	VS048250	0.03	24.90	0.21	3.49
	958.3	959.22	0.92	VS048251	0.01	22.30	0.02	3.39
	959.22	960.27	1.05	VS048252	0.02	23.70	0.02	3.21
	960.27	961.24	0.97	VS048253	0.01	22.50	0.01	3.38
	961.24	962.4	1.16	VS048254	0.02	46.80	0.03	4.01
	962.4	963.01	0.61	VS048255	0.02	51.00	0.02	4.26

D zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	S (%)	Density (g/cm ³)
	963.01	963.92	0.91	VS048257	0.05	32.80	0.16	3.32
	963.92	964.8	0.88	VS048258	0.13	29.20	0.20	3
	964.8	965.78	0.98	VS048259	0.01	7.82	0.36	2.9
	965.78	966.76	0.98	VS048260	0.03	10.75	0.25	2.91
	966.76	967.76	1	VS048261	0.03	31.10	0.13	2.88
	967.76	968.76	1	VS048262	0.73	36.80	2.03	3.35
	968.76	969.7	0.94	VS048263	0.10	8.75	0.25	2.89
	969.7	970.53	0.83	VS048265	1.01	49.00	1.92	4.35
	970.53	971.36	0.83	VS048266	0.69	48.70	1.05	3.71
	971.36	972.28	0.92	VS048267	0.04	7.25	0.04	2.8
	972.28	973.49	1.21	VS048268	0.05	14.40	0.03	3.14
	973.49	974.7	1.21	VS048269	0.13	8.83	0.09	2.88
	974.7	975.51	0.81	VS048270	0.02	24.20	0.01	3.18
	975.51	976.32	0.81	VS048271	0.58	29.70	0.62	3.14
	976.32	977.58	1.26	VS048273	1.27	21.40	2.55	3.33
	977.58	978.73	1.15	VS048274	1.18	16.55	2.19	2.72
	978.73	980.04	1.31	VS048275	0.99	27.70	1.86	3.19
	980.04	981.67	1.63	VS048276	0.10	2.33	0.17	2.57
	981.67	983.3	1.63	VS048277	0.08	6.34	0.64	2.6
	983.3	983.96	0.66	VS048278	0.18	5.68	2.38	2.6
	983.96	985.5	1.54	VS048279	0.37	10.70	1.35	2.6
	1025.1	1026.01	0.91	VS048847	0.38	4.46	0.39	2.69
	1026.01	1026.92	0.91	VS048848	0.21	4.34	0.22	2.79
	1026.92	1028	1.08	VS048849	0.67	8.60	0.71	2.9
	1028	1029	1	VS048850	0.08	5.59	0.34	2.78
	1029	1029.6	0.6	CORELOSS	0.00	0.00	0.00	2.9
	1029.6	1030.68	1.08	VS048851	0.85	11.00	1.12	2.97
VDD24029C	1030.68	1031.22	0.54	VS048852	0.29	7.64	0.30	2.88
	1031.22	1032.22	1	VS048853	0.69	32.20	0.76	3.79
	1032.22	1032.98	0.76	VS048855	0.61	8.72	0.67	2.79
	1032.98	1034.36	1.38	VS048856	0.09	3.97	1.48	2.87
	1034.36	1035.28	0.92	VS048857	0.05	4.62	0.24	2.92
	1035.28	1036.2	0.92	VS048858	0.10	3.32	0.40	2.77
	1036.2	1037.12	0.92	VS048859	0.03	3.72	0.26	2.9

D zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	S (%)	Density (g/cm ³)
	1037.12	1038.4	1.28	VS048860	0.02	3.01	0.51	2.85
	1038.4	1039.68	1.28	VS048861	0.01	1.24	0.14	2.76
	1039.68	1040.96	1.28	VS048862	0.02	1.14	0.30	2.72
	1040.96	1042.24	1.28	VS048863	0.06	2.31	0.16	2.79
	1042.24	1043.52	1.28	VS048865	0.05	2.67	0.22	2.75
	1043.52	1044.8	1.28	VS048866	0.25	4.48	0.98	2.72
	1044.8	1046.08	1.28	VS048867	0.04	1.54	0.56	2.7
	1046.08	1047.4	1.32	VS048868	0.06	2.70	0.42	2.71
	1047.4	1048.45	1.05	VS048869	0.67	43.20	2.52	4.14
	1048.45	1049.5	1.05	VS048870	2.17	45.80	3.41	3.94
	1049.5	1050.55	1.05	VS048871	1.84	56.30	2.83	4.35
	1050.55	1051.6	1.05	VS048873	1.07	50.40	2.32	4.4
	1051.6	1051.9	0.3	VS048875	0.46	14.75	2.73	3.02
	1051.9	1053.04	1.14	VS048876	1.13	46.60	1.52	4.11
	1053.04	1054.16	1.12	VS048877	0.39	21.10	4.59	2.97
	989.43	990.2	0.77	VS055179	0.17	39.40	3.70	3.26
	990.2	990.78	0.58	VS055180	0.70	17.25	3.75	3.43
	990.78	991.68	0.9	VS055181	1.15	46.50	2.32	4.59
	991.68	992.6	0.92	VS055182	1.07	60.40	3.20	4.35
	992.6	993.53	0.93	VS055183	0.87	46.00	2.01	4.35
	993.53	994.52	0.99	VS055185	1.21	59.50	2.68	4.53
	994.52	995.1	0.58	VS055186	0.76	12.65	2.52	2.86
	995.1	995.86	0.76	VS055187	0.84	48.30	2.88	4.01
	995.86	996.66	0.8	VS055188	1.08	49.60	3.30	4.27
VDD24029D	996.66	997.9	1.24	VS055189	0.32	13.85	0.68	2.89
	997.9	998.64	0.74	VS055190	0.10	44.10	0.36	4.01
	998.64	999.84	1.2	VS055192	0.03	9.15	0.14	2.85
	999.84	1001.01	1.17	VS055193	0.01	8.56	0.05	2.95
	1001.01	1002.1	1.09	VS055194	0.09	8.39	0.32	2.96
	1002.1	1002.53	0.43	VS055195	0.01	11.35	0.15	3
	1002.53	1003.64	1.11	VS055196	0.02	7.54	0.09	2.8
	1003.64	1004.74	1.1	VS055197	0.01	8.47	0.17	2.88
	1004.74	1005.97	1.23	VS055198	0.02	9.96	0.25	2.95
	1005.97	1007	1.03	VS055199	0.01	9.89	0.21	2.87
	1007	1008.1	1.1	VS055201	0.26	24.70	0.60	3.51

D zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	S (%)	Density (g/cm ³)
VDD24055C	1008.1	1009.13	1.03	VS055202	0.19	17.10	0.44	3.79
	1009.13	1010.18	1.05	VS055203	1.34	47.70	4.48	4.41
	1010.18	1011.05	0.87	VS055204	1.16	42.20	1.98	3.93
	1034.16	1035.01	0.85	VS052561	0.10	10.55	0.40	2.82
	1035.01	1036.05	1.04	VS052562	0.05	9.07	0.55	2.82
	1036.05	1037.08	1.03	VS052563	0.21	8.93	0.89	2.79
	1037.08	1038.06	0.98	VS052564	0.21	6.25	0.54	2.92
	1038.06	1039.12	1.06	VS052565	0.10	4.02	0.26	2.76
	1039.12	1040.11	0.99	VS052567	0.49	35.80	0.71	4.06
	1040.11	1041.13	1.02	VS052568	0.19	35.20	0.25	3.67
	1041.13	1042.03	0.9	VS052569	0.01	8.55	0.02	2.97
	1042.03	1042.95	0.92	VS052570	0.00	7.89	0.01	2.86
	1042.95	1043.75	0.8	VS052571	0.00	8.36	0.01	2.83
	1043.75	1044.64	0.89	VS052572	0.00	8.23	0.01	3.1
	1044.64	1044.95	0.31	CORELOSS	0.00	0.00	0.00	3
	1044.95	1046.35	1.4	VS052573	0.00	9.80	0.01	2.85
	1046.35	1047.37	1.02	VS052575	0.00	41.00	0.02	4.03
	1047.37	1048	0.63	VS052576	0.10	33.90	0.14	3.98
	1048	1048.47	0.47	VS052577	0.04	11.70	0.35	3.42
	1048.47	1049.36	0.89	VS052578	0.10	11.55	0.63	2.98
	1049.36	1050.25	0.89	VS052579	0.27	12.15	0.27	3.11
	1050.25	1051.15	0.9	VS052580	1.15	47.30	1.14	3.93
	1051.15	1051.96	0.81	VS052581	1.20	35.00	1.37	3.66
	1051.96	1052.83	0.87	VS052583	1.16	36.80	1.43	4.06
	1052.83	1053.3	0.47	VS052584	0.20	20.40	0.20	3.29
	1053.3	1054.25	0.95	VS052585	0.00	12.90	0.01	3
	1054.25	1055.15	0.9	VS052586	0.00	11.65	0.10	3.03
	1055.15	1056.21	1.06	VS052587	0.00	32.70	0.10	3.33
	1056.21	1057.3	1.09	VS052588	0.01	15.75	0.18	2.8
	1057.3	1058.25	0.95	VS052590	1.25	31.40	1.61	3.11
1058.25	1059.2	0.95	VS052591	2.05	35.40	2.14	3.13	
1059.2	1060.25	1.05	VS052592	2.84	53.60	3.10	4.29	
1060.25	1060.8	0.55	CORELOSS	0.00	0.00	0.00	3.8	
1060.8	1061.5	0.7	VS052593	2.75	49.20	2.98	3.8	
1061.5	1062.06	0.56	VS052594	1.97	35.90	1.90	3.8	
1062.06	1064.2	2.14	CORELOSS	0.00	0.00	0.00	3.8	

D zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	S (%)	Density (g/cm ³)
	1064.2	1064.5	0.3	VS052595	3.02	30.40	3.17	3.8
	1064.5	1065.45	0.95	VS052597	0.42	14.50	0.47	2.41
	1065.45	1066.27	0.82	VS052598	0.29	8.61	0.34	2.61
	1066.27	1067.24	0.97	VS052599	0.41	12.45	0.50	2.7
	1067.24	1068.08	0.84	VS052600	0.47	14.20	0.59	2.77
	1046.74	1047.38	0.64	VS052953	0.16	10.45	0.50	3
	1047.38	1047.91	0.53	VS052954	0.91	43.00	2.33	3.95
	1047.91	1048.88	0.97	VS052955	0.05	2.06	0.13	2.78
	1048.88	1049.93	1.05	VS052957	0.27	5.74	0.35	3.05
	1049.93	1051.03	1.1	VS052958	0.04	1.89	0.07	2.7
	1051.03	1051.85	0.82	VS052959	0.08	3.24	1.60	2.78
	1051.85	1052.74	0.89	VS052960	0.01	1.44	0.01	2.76
	1052.74	1053.68	0.94	VS052961	0.03	1.63	0.02	2.68
	1053.68	1054.63	0.95	VS052962	0.10	1.43	0.07	2.79
	1054.63	1055.48	0.85	VS052963	0.03	2.48	0.01	2.74
	1055.48	1056.27	0.79	VS052964	2.28	31.70	2.19	3.59
	1056.27	1057.07	0.8	VS052965	0.05	2.50	0.15	2.76
	1057.07	1057.93	0.86	VS052966	0.01	2.53	0.05	2.66
	1057.93	1059	1.07	VS052968	2.93	43.40	3.10	3.59
	1059	1060.05	1.05	VS052969	2.65	48.50	2.75	3.79
VDD24055D	1060.05	1060.78	0.73	VS052970	1.34	45.50	1.29	4.05
	1060.78	1061.56	0.78	VS052971	1.50	51.50	1.51	4.29
	1061.56	1062.58	1.02	VS052972	0.01	43.40	0.02	3.73
	1062.58	1063.6	1.02	VS052973	0.01	45.20	0.01	3.92
	1063.6	1064.41	0.81	VS052975	0.00	56.30	0.01	4.4
	1064.41	1065.21	0.8	VS052976	0.00	24.40	0.01	3.48
	1065.21	1066.02	0.81	VS052977	0.00	13.70	0.01	3.01
	1066.02	1066.75	0.73	VS052978	0.00	46.10	0.01	4.09
	1066.75	1067.36	0.61	VS052979	0.15	61.50	0.21	4.49
	1067.36	1068.17	0.81	VS052980	0.30	43.80	0.33	3.87
	1068.17	1068.9	0.73	VS052982	0.33	17.20	0.32	3.04
	1068.9	1069.75	0.85	VS052983	0.40	14.40	0.53	2.94
	1069.75	1070.6	0.85	VS052984	0.40	13.70	0.55	3
	1070.6	1071.48	0.88	VS052985	0.46	14.40	0.71	3
	1071.48	1071.78	0.3	CORELOSS	0.00	0.00	0.00	3
	1071.78	1072.35	0.57	VS052986	0.62	29.40	0.82	3.63

D zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	S (%)	Density (g/cm ³)
VDD24055E	1052.4	1053.3	0.9	VS053142	0.12	9.21	2.16	2.99
	1053.3	1054.5	1.2	VS053144	0.22	32.20	3.07	3.43
	1054.5	1055.71	1.21	VS053145	0.96	35.60	1.78	3.27
	1055.71	1056.97	1.26	VS053146	0.17	5.90	0.32	2.85
	1056.97	1058.24	1.27	VS053147	0.01	1.06	0.04	2.8
	1058.24	1059.49	1.25	VS053148	0.17	2.04	0.32	2.78
	1059.49	1060.75	1.26	VS053149	0.42	4.01	0.56	2.85
	1060.75	1062.02	1.27	VS053150	0.04	1.04	0.03	2.74
	1062.02	1063.27	1.25	VS053151	0.06	0.74	0.08	2.75
	1063.27	1064.53	1.26	VS053152	0.05	1.21	0.04	2.79
	1064.53	1065.11	0.58	VS053154	2.11	32.80	2.31	3.61
	1065.11	1066	0.89	VS053155	0.02	1.66	0.03	2.71
	1066	1066.89	0.89	VS053156	0.14	7.35	1.58	2.79
	1066.89	1067.14	0.25	CORELOSS	0.00	0.00	0.00	2.8
	1067.14	1068.07	0.93	VS053157	0.06	3.22	0.14	3
	1068.07	1069.25	1.18	VS053158	2.43	40.40	2.39	3.97
	1069.25	1070.43	1.18	VS053159	1.84	52.40	1.78	4.26
	1070.43	1071.6	1.17	VS053160	0.01	45.80	0.02	3.89
	1071.6	1072.79	1.19	VS053162	0.01	46.60	0.02	4.04
	1072.79	1073.97	1.18	VS053163	0.00	44.20	0.01	4.13
1073.97	1075.15	1.18	VS053164	0.00	19.60	0.04	3.15	
1075.15	1076.33	1.18	VS053165	0.00	42.10	0.03	4.46	
1076.33	1077.55	1.22	VS053166	0.11	53.20	0.13	4.5	
1077.55	1078	0.45	CORELOSS	0.00	0.00	0.00	4.1	
1078	1078.3	0.3	VS053167	0.17	51.00	0.33	4.34	
VDD24055F	1040.75	1041.9	1.15	VS053033	0.14	6.93	0.42	2.78
	1041.9	1043.08	1.18	VS053034	0.08	11.85	0.44	2.71
	1043.08	1044.27	1.19	VS053035	0.25	29.30	0.82	3.95
	1044.27	1045.41	1.14	VS053036	0.84	33.70	1.51	3.76
	1045.41	1046.52	1.11	VS053037	0.75	26.40	1.46	3.11
	1046.52	1047.58	1.06	VS053039	0.20	1.21	0.41	2.67
	1047.58	1048.54	0.96	VS053040	0.57	10.60	0.64	3.23
	1048.54	1049.6	1.06	VS053041	0.04	4.21	0.28	2.88
	1049.6	1050.88	1.28	VS053042	1.10	30.70	2.21	3.41
	1050.88	1052.15	1.27	VS053043	0.64	31.20	1.53	3.23
1052.15	1053.44	1.29	VS053044	0.92	36.80	0.97	3.9	

D zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	S (%)	Density (g/cm ³)
	1053.44	1054.72	1.28	VS053045	1.21	30.50	1.45	3.47
	1054.72	1056	1.28	VS053046	0.02	40.40	0.15	4.23
	1056	1057.22	1.22	VS053048	0.00	13.00	0.19	3.14
	1057.22	1058.3	1.08	VS053049	0.01	20.40	0.09	2.81
	1058.3	1059.5	1.2	VS053050	0.00	24.10	0.34	3.1
	1059.5	1060.55	1.05	VS053051	0.01	52.10	0.22	3.85
	1060.55	1061.46	0.91	VS053052	0.26	16.10	0.46	2.82
	1061.46	1062.4	0.94	VS053053	0.27	13.40	0.38	2.81
	1062.4	1063.42	1.02	VS053054	1.22	31.20	1.42	3.33
	1063.42	1064.66	1.24	VS053055	1.68	32.60	2.11	3.63
	1064.66	1065.85	1.19	VS053057	0.25	17.00	0.31	2.65
	1065.85	1067.15	1.3	VS053058	0.71	23.10	0.74	2.89
	1107	1107.84	0.84	VS055264	1.77	16.95	2.74	3.02
	1107.84	1108.62	0.78	VS055265	1.54	41.80	2.41	3.77
	1108.62	1109.82	1.2	VS055267	0.55	5.54	0.86	2.94
	1109.82	1110.8	0.98	VS055268	0.05	2.06	0.06	2.64
	1110.8	1111.7	0.9	VS055269	0.17	4.52	0.23	2.81
	1111.7	1112.9	1.2	VS055270	0.24	9.44	0.45	3.09
	1112.9	1113.66	0.76	VS055271	1.89	43.60	2.06	3.98
	1113.66	1114.25	0.59	VS055272	4.59	47.50	4.98	4.08
	1114.25	1114.7	0.45	VS055273	0.36	4.26	0.45	3
	1114.7	1115.4	0.7	VS055274	2.32	52.00	2.59	4.16
	1115.4	1116.2	0.8	VS055275	3.14	51.70	3.67	4.34
	1116.2	1116.8	0.6	VS055276	0.28	40.60	0.35	4.2
VDD24055G	1116.8	1117.75	0.95	VS055277	0.01	43.90	0.05	4.24
	1117.75	1118.75	1	VS055279	0.01	37.50	0.08	3.98
	1118.75	1119.64	0.89	VS055280	0.02	52.00	0.18	4.02
	1119.64	1120.94	1.3	VS055281	0.23	42.00	0.43	4.39
	1120.94	1122.12	1.18	VS055282	0.22	18.60	0.35	3.06
	1122.12	1122.87	0.75	VS055283	1.02	18.05	1.35	3.04
	1122.87	1123.96	1.09	VS055284	1.89	50.50	2.35	4.27
	1123.96	1125.04	1.08	VS055285	2.18	40.40	2.30	4.11
	1125.04	1125.68	0.64	VS055286	4.53	52.70	4.96	4.54
	1125.68	1126.25	0.57	VS055288	0.18	15.85	0.64	3.14
	1126.25	1126.55	0.3	CORELOSS	0.00	0.00	0.00	3
	1126.55	1127.6	1.05	VS055289	0.31	12.75	0.63	2.98

D zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	S (%)	Density (g/cm ³)
	1127.6	1128.7	1.1	VS055290	0.34	12.90	0.59	3.06
	1128.7	1129.88	1.18	VS055291	0.35	13.45	0.57	3.01
	1129.88	1130.52	0.64	VS055292	2.84	53.30	2.81	4.55
	1130.52	1131.82	1.3	VS055293	1.40	34.00	1.41	4.08
	1131.82	1133	1.18	VS055294	0.72	18.55	0.83	2.96
	1133	1134.02	1.02	VS055295	2.03	38.70	2.06	3.62
	1134.02	1134.94	0.92	VS055296	0.04	10.05	0.06	3.02
	1134.94	1136.05	1.11	VS055297	2.01	34.30	2.01	3.71
	1136.05	1137.05	1	VS055299	1.42	36.50	1.49	3.75
	1137.05	1138.1	1.05	VS055300	1.14	40.10	1.14	3.42
	1138.1	1138.5	0.4	CORELOSS	0.00	0.00	0.00	3.7
	1138.5	1139.55	1.05	VS055301	0.36	17.70	0.38	3.7
	1139.55	1139.9	0.35	VS055302	0.24	34.60	0.26	4.15
	1139.9	1141.1	1.2	VS055303	0.32	25.30	0.32	2.92
	1141.1	1142.24	1.14	VS055304	0.11	15.40	0.11	2.94
	1142.24	1143.08	0.84	VS055305	0.74	48.40	0.73	4.3
	1143.08	1143.92	0.84	VS055306	1.40	38.10	1.34	4.17
	1143.92	1144.7	0.78	VS055308	0.57	31.40	0.53	3.59
	1144.7	1145.4	0.7	VS055309	0.09	17.80	0.10	2.94
	1145.4	1146.1	0.7	VS055310	0.18	10.60	0.17	2.96
	1146.1	1147.1	1	VS055311	0.96	41.10	0.93	3.85
	1147.1	1148.06	0.96	VS055312	1.89	44.10	1.77	3.91
	1148.06	1149.28	1.22	VS055313	3.35	52.00	3.83	4.07
	1149.28	1150.2	0.92	VS055315	0.11	9.78	0.27	2.7

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
VDD0127B	1236.06	1237.25	1.19	VS054159	0.60	12.25	0.57	2.99
	1237.25	1238.55	1.3	VS054160	0.48	11.05	0.48	3
	1238.55	1239.62	1.07	VS054161	0.19	11.65	0.20	3.01
	1239.62	1240.92	1.3	VS054162	1.36	11.70	1.22	3.06
	1240.92	1242.22	1.3	VS054163	0.77	11.45	0.71	3.05
	1242.22	1243.46	1.24	VS054164	0.82	13.40	0.81	3.13
	1243.46	1244.76	1.3	VS054166	0.40	11.70	0.41	3.02
	1244.76	1246.02	1.26	VS054167	0.65	11.35	0.61	3.03
	1246.02	1247.21	1.19	VS054168	1.13	11.70	1.02	3.06
	1247.21	1248.5	1.29	VS054169	1.51	11.85	1.34	2.98
	1248.5	1249.35	0.85	VS054170	1.68	11.40	1.64	3.01
	1249.35	1249.92	0.57	VS054171	0.85	12.15	0.85	3.23
	1249.92	1251.2	1.28	VS054173	0.24	11.35	0.22	2.99
	1251.2	1252.16	0.96	VS054174	0.37	12.80	0.34	3.05
	1252.16	1253.4	1.24	VS054175	0.40	13.00	0.37	3.09
	1253.4	1254.65	1.25	VS054176	0.24	11.85	0.20	3.11
	1254.65	1255.95	1.3	VS054177	0.30	11.60	0.28	3.03
	1255.95	1257.09	1.14	VS054179	0.82	11.75	0.69	3.17
	1257.09	1258.07	0.98	VS054180	0.35	10.65	0.34	3.08
	1258.07	1259.21	1.14	VS054181	0.32	11.25	0.33	3.06
	1259.21	1260.5	1.29	VS054182	0.19	11.80	0.15	3.02
	1260.5	1261.75	1.25	VS054184	0.43	12.70	0.39	3.1
	1261.75	1262.94	1.19	VS054185	0.60	12.00	0.54	3.11
	1262.94	1264.12	1.18	VS054186	0.10	11.90	0.10	3.09
	1264.12	1265.1	0.98	VS054187	0.12	11.80	0.14	2.94
	1265.1	1266.27	1.17	VS054188	0.23	10.25	0.22	3.07
	1266.27	1267.52	1.25	VS054189	0.04	12.55	0.05	3.15
	1267.52	1268.74	1.22	VS054190	0.06	13.60	0.06	3.07
	1268.74	1270.03	1.29	VS054191	0.19	12.75	0.16	3.04
	1270.03	1271.33	1.3	VS054192	0.08	14.35	0.07	3.13
	1271.33	1272.63	1.3	VS054194	0.32	13.55	0.30	3.08
	1272.63	1273.92	1.29	VS054195	0.03	14.60	0.04	3.12
	1273.92	1275.18	1.26	VS054196	0.04	14.20	0.05	3.13
1275.18	1276.48	1.3	VS054197	0.36	12.50	0.34	3.09	
1276.48	1277.74	1.26	VS054198	0.37	13.50	0.32	3.07	
1277.74	1279.04	1.3	VS054199	0.73	11.15	0.64	2.94	
1279.04	1280.34	1.3	VS054200	0.15	13.80	0.13	3.13	
1280.34	1281.59	1.25	VS054201	0.34	11.90	0.31	3.12	
1281.59	1282.82	1.23	VS054203	0.52	12.60	0.49	3.05	

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm³)
	1282.82	1284.04	1.22	VS054204	0.04	13.30	0.01	3.06
	1284.04	1285.3	1.26	VS054205	0.02	10.95	0.03	3
	1285.3	1286.5	1.2	VS054206	0.02	11.80	0.02	3.03
	1286.5	1287.64	1.14	VS054207	0.68	9.44	0.67	2.97
	1287.64	1288.73	1.09	VS054208	0.97	10.45	0.99	2.96
	1288.73	1289.94	1.21	VS054209	0.42	9.41	0.45	2.99
	1289.94	1290.8	0.86	VS054210	0.64	10.85	0.65	3.03
	1290.8	1292.1	1.3	VS054211	0.66	10.15	0.70	3
	1292.1	1293.04	0.94	VS054213	0.37	9.62	0.39	2.99
	1293.04	1294.3	1.26	VS054214	0.50	10.35	0.50	3
	1294.3	1295.5	1.2	VS054215	0.33	12.35	0.32	3.04
	1295.5	1295.96	0.46	VS054216	2.82	38.40	3.21	3.7
	1295.96	1296.8	0.84	VS054218	0.29	12.60	0.32	3.01
	1296.8	1297.6	0.8	VS054219	0.00	11.70	0.01	3.01
	1297.6	1298.84	1.24	VS054220	0.12	9.26	0.12	3.02
	1298.84	1299.96	1.12	VS054221	0.13	9.14	0.15	2.91
	1299.96	1301.26	1.3	VS054222	0.09	10.45	0.09	3
	1301.26	1302.54	1.28	VS054223	0.08	10.55	0.08	2.94
	1302.54	1303.84	1.3	VS054224	0.14	7.22	0.16	2.93
	1303.84	1305.14	1.3	VS054225	0.06	9.18	0.07	2.91
	1305.14	1306.44	1.3	VS054226	0.01	8.62	0.02	2.9
	1306.44	1307.74	1.3	VS054228	0.05	8.57	0.06	2.86
	1307.74	1309.02	1.28	VS054229	0.21	10.15	0.22	2.93
	1309.02	1310.23	1.21	VS054230	0.42	10.55	0.47	2.88
	1310.23	1311.3	1.07	VS054231	0.62	8.25	0.73	3.01
	1311.3	1312.26	0.96	VS054232	6.50	14.20	7.19	3.14
	1312.26	1312.9	0.64	VS054233	4.41	12.75	4.71	3.06
	1312.9	1314.19	1.29	VS054235	0.66	4.84	0.72	2.8
	1314.19	1315.48	1.29	VS054236	2.20	6.97	2.36	2.79
	1315.48	1316.72	1.24	VS054237	1.23	6.22	1.44	2.86
	1316.72	1317.87	1.15	VS054238	1.74	10.25	1.90	2.83
	1317.87	1319.07	1.2	VS054239	0.41	5.26	0.48	2.82
	1319.07	1320.26	1.19	VS054240	0.11	5.95	0.09	2.81
	1320.26	1321.41	1.15	VS054241	0.42	11.50	0.40	2.99
	1321.41	1322.32	0.91	VS054242	0.76	12.95	0.89	3.06
	1322.32	1323.5	1.18	VS054243	0.51	11.60	0.79	2.91

B zone								
Hole ID	Depth from	Depth to	Sample length	Sample ID	Cu	Fe	Ag	Density
			(m)		(%)	(%)	(g/t)	(g/cm³)
	1323.5	1324.74	1.24	VS054245	0.05	9.66	0.04	2.93
	1324.74	1325.9	1.16	VS054246	0.05	10.50	0.07	2.97
	1325.9	1327	1.1	VS054247	0.24	10.75	0.31	3.09
	1327	1328.25	1.25	VS054248	0.46	6.76	0.84	2.83
	1328.25	1329.55	1.3	VS054249	0.21	4.52	0.26	2.82
	1329.55	1330.75	1.2	VS054250	0.40	4.56	0.64	2.75
	1330.75	1332.03	1.28	VS054251	0.10	3.02	0.21	2.73
	1332.03	1333.12	1.09	VS054252	0.10	3.92	0.24	2.78
	1333.12	1334.2	1.08	VS054253	0.33	4.71	0.52	2.78
	1334.2	1335.32	1.12	VS054255	0.84	5.69	1.86	2.85
	1335.32	1336.52	1.2	VS054256	0.79	4.76	1.46	2.83
	1336.52	1337.78	1.26	VS054257	0.94	5.15	1.46	2.75
	1337.78	1339	1.22	VS054258	0.42	3.57	0.74	2.79
	1339	1340.15	1.15	VS054259	0.44	3.64	0.64	2.74
	1340.15	1341.3	1.15	VS054260	0.52	4.26	1.18	2.73
	1341.3	1342.54	1.24	VS054261	0.61	4.04	1.10	2.77
	1342.54	1343.66	1.12	VS054262	0.61	3.80	0.89	2.8
	1343.66	1344.69	1.03	VS054263	0.33	3.17	0.40	2.74
	1344.69	1345.76	1.07	VS054265	0.21	2.78	0.34	2.79
	1345.76	1346.75	0.99	VS054266	0.80	6.26	1.17	2.79
	1346.75	1347.8	1.05	VS054267	1.26	10.25	1.50	2.88
	174.2	175.23	1.03	VS015788	0.32	14.80	0.91	3
	175.23	176.5	1.27	VS015789	2.22	18.55	5.91	3
	176.5	177.8	1.3	VS015790	0.90	14.75	1.86	3.13
	177.8	179.1	1.3	VS015791	0.60	15.15	1.18	2.86
	179.1	180.3	1.2	VS015792	0.25	16.35	0.45	3
	180.3	181.6	1.3	VS015793	0.24	15.00	0.47	3.07
	181.6	182.5	0.9	VS015794	1.36	16.60	2.32	3
VDD21033	182.5	183.7	1.2	VS015795	0.37	15.55	0.68	3
	183.7	185	1.3	VS015796	0.91	11.75	1.54	2.96
	185	186.2	1.2	VS015797	0.94	13.85	1.45	3
	186.2	187.31	1.11	VS015798	1.69	15.35	2.88	2.84
	187.31	188.4	1.09	VS015799	2.12	16.60	3.59	3.08
	188.4	189.6	1.2	VS015800	0.66	16.05	1.18	3
	189.6	190.9	1.3	VS015801	1.36	17.90	3.69	3.07
	190.9	191.9	1	VS015802	0.86	13.65	2.16	3

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
VDD22013	503.6	504.9	1.3	VS022568	0.25	18.65	0.41	3.22
	504.9	506.25	1.35	VS022569	0.09	17.95	0.17	3.18
	506.25	507.55	1.3	VS022570	0.20	17.05	0.40	3.14
	507.55	508.75	1.2	VS022571	0.35	18.80	0.71	3.2
	508.75	509.9	1.15	VS022572	0.56	19.05	1.10	3.36
	509.9	511.2	1.3	VS022573	0.37	17.55	0.85	3.21
	511.2	512.45	1.25	VS022574	0.35	19.90	0.79	3.1
	512.45	513.75	1.3	VS022575	0.51	18.30	1.08	3.1
	513.75	515	1.25	VS022577	0.46	19.95	1.12	3.24
	515	516	1	VS022578	0.57	18.30	1.42	3.14
	516	517.3	1.3	VS022579	0.90	16.70	2.31	3.08
	517.3	518.6	1.3	VS022580	0.47	14.40	1.20	3.08
	518.6	519.9	1.3	VS022581	0.62	13.85	1.70	3.05
	519.9	521.15	1.25	VS022583	0.34	15.35	0.88	3.12
	521.15	522.45	1.3	VS022584	0.56	14.80	1.40	3.09
	522.45	523.75	1.3	VS022585	0.62	13.75	1.68	3.1
	523.75	525.05	1.3	VS022586	0.49	12.90	1.32	3.05
	525.05	526.05	1	VS022587	0.94	13.15	2.32	3.11
	526.05	527.35	1.3	VS022588	0.34	13.50	0.91	3.09
	527.35	528.55	1.2	VS022589	0.72	13.10	1.89	3.03
	528.55	529.8	1.25	VS022590	0.59	13.70	1.58	3.08
	529.8	531	1.2	VS022591	0.84	17.35	2.54	3.28
	531	531.9	0.9	VS022592	0.73	19.35	2.17	3.1
	531.9	532.6	0.7	VS022594	0.40	25.40	1.79	3.1
	532.6	533.2	0.6	VS022595	1.28	15.55	4.21	3.1
	533.2	534.5	1.3	VS022596	0.56	16.40	1.84	3.1
	534.5	535.7	1.2	VS022597	1.12	14.70	2.92	3.1
	535.7	536.7	1	VS022598	2.37	13.05	6.69	3.11
	536.7	538	1.3	VS022599	2.15	20.60	8.50	3.22
	538	539.35	1.35	VS022600	1.87	16.55	6.97	3.12
	539.35	540.6	1.25	VS022601	0.71	21.80	2.37	3.13
	540.6	541.3	0.7	VS022602	1.14	18.40	3.33	3.24
	541.3	542.15	0.85	VS022603	0.32	14.85	0.97	3.1
542.15	542.85	0.7	VS022605	1.52	10.50	4.25	3.03	
542.85	543.9	1.05	VS022606	2.34	43.90	6.53	4.31	
543.9	545	1.1	VS022607	4.05	31.40	12.30	4.1	

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	545	545.6	0.6	VS022608	2.07	14.05	6.07	3.3
	545.6	546.5	0.9	VS022609	1.34	14.65	4.55	3.3
	546.5	547.15	0.65	VS022610	2.96	45.80	9.24	4.41
	547.15	548.35	1.2	VS022611	4.83	53.00	14.10	4.49
	548.35	549.1	0.75	VS022613	1.51	30.00	4.25	4.1
	549.1	550.25	1.15	VS022614	2.14	13.65	6.23	3.23
	550.25	551.55	1.3	VS022615	1.41	14.65	4.24	3.3
	551.55	552.6	1.05	VS022616	1.46	45.10	3.85	4
	552.6	553.75	1.15	VS022617	2.62	19.10	7.59	3.36
	553.75	554.7	0.95	VS022618	4.33	46.30	12.00	4.17
	554.7	555.05	0.35	VS022619	2.00	42.70	5.83	4
	555.05	556.3	1.25	VS022620	1.55	58.10	4.57	3.91
	556.3	557.3	1	VS022622	0.63	57.30	1.84	4.57
	557.3	557.95	0.65	VS022623	0.43	56.40	1.43	4
	557.95	558.75	0.8	VS022624	0.58	43.90	1.69	3.99
	558.75	559.5	0.75	VS022625	0.31	52.50	1.08	4.28
	559.5	560.8	1.3	VS022626	0.31	28.30	1.18	3.5
	560.8	561.7	0.9	VS022627	0.36	24.20	1.20	3.48
	561.7	562.95	1.25	VS022629	0.40	21.30	1.07	3.38
	562.95	564.2	1.25	VS022630	0.35	19.10	1.14	3.32
	564.2	565.2	1	VS022631	0.33	16.75	0.82	3.3
	565.2	566.35	1.15	VS022632	0.18	14.20	0.57	3.3
VDD23014	270.3	271	0.7	VS032012	0.66	10.75	1.86	2.93
	271	272.05	1.05	VS032013	1.44	13.35	5.13	2.7
	272.05	273.25	1.2	VS032014	1.36	11.30	3.35	3.02
	273.25	274.25	1	VS032015	0.93	11.90	1.75	3.01
	274.25	275.3	1.05	VS032016	1.15	10.50	2.47	3.1
	275.3	276.3	1	VS032018	0.72	17.95	2.03	3.15
	276.3	277.3	1	VS032019	0.09	13.55	0.33	2.8
	277.3	278.55	1.25	VS032020	0.02	13.60	0.05	2.8
	278.55	279.8	1.25	VS032021	0.02	12.70	0.07	2.8
	279.8	280.7	0.9	VS032022	0.02	11.95	0.08	2.8
	280.7	281.75	1.05	VS032023	1.68	17.60	4.59	3.4
	281.75	282.9	1.15	VS032024	0.69	13.25	2.51	2.98
	282.9	283.95	1.05	VS032026	1.28	17.05	4.01	3.11
	283.95	285.15	1.2	VS032027	0.61	18.20	1.78	3.18

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
VDD23019	285.15	286.35	1.2	VS032028	0.60	15.40	1.72	3.07
	619.1	620	0.9	VS033156	0.13	10.10	0.60	3.2
	620	620.92	0.92	VS033158	0.49	9.32	2.40	3.14
	620.92	621.76	0.84	VS033159	1.18	5.72	5.23	3.34
	621.76	622.75	0.99	VS033161	0.03	9.91	0.18	3.2
	622.75	623.88	1.13	VS033162	0.02	12.85	0.11	3.2
	623.88	626.1	2.22	VS033163	0.05	12.90	0.22	3.2
	626.1	629	2.9	VS033164	0.01	13.20	0.06	3.2
	629	630.18	1.18	VS033165	0.03	13.85	0.17	3.2
	630.18	631.4	1.22	VS033166	0.08	14.40	0.33	3.2
	631.4	632.3	0.9	VS033167	0.02	14.25	0.11	3.2
	632.3	633	0.7	VS033168	0.10	13.80	2.63	3.2
	633	633.69	0.69	VS033169	0.06	15.65	0.27	3.2
	633.69	634.62	0.93	VS033171	1.86	17.05	9.15	3.3
	634.62	635.06	0.44	VS033172	1.03	14.05	2.99	3.04
	635.06	635.55	0.49	VS033173	1.41	16.90	3.94	3.41
	635.55	636.82	1.27	VS033175	0.15	16.05	1.52	3.2
	636.82	638	1.18	VS033176	0.39	14.60	1.21	3.2
	638	639.1	1.1	VS033177	0.35	16.30	1.34	3.2
	639.1	639.76	0.66	VS033178	0.55	16.80	1.24	3.2
	639.76	641	1.24	VS033180	1.25	16.40	6.89	3.23
	641	642	1	VS033181	1.70	16.40	4.51	3.17
	642	642.8	0.8	VS033182	0.89	15.40	2.41	3.3
	642.8	643.9	1.1	VS033183	0.39	15.10	1.00	4.89
	643.9	645.14	1.24	VS033184	0.93	14.70	2.61	3.3
	645.14	646.05	0.91	VS033185	1.36	15.90	3.67	2.98
	646.05	647	0.95	VS033186	1.18	14.70	3.37	3.06
	647	647.85	0.85	VS033187	2.27	15.55	6.03	3.37
	647.85	649	1.15	VS033188	1.72	14.40	4.55	3.27
	649	649.8	0.8	VS033189	1.18	13.85	3.11	3.24
	649.8	650.68	0.88	VS033190	1.23	12.25	3.30	3.38
	650.68	651.6	0.92	VS033191	1.29	13.20	3.51	3.37
651.6	652.45	0.85	VS033192	0.78	13.50	2.20	3.33	
652.45	653.1	0.65	VS033193	0.78	11.20	2.16	3.79	
653.1	654.4	1.3	VS033195	0.37	13.50	1.01	3.2	
654.4	655.7	1.3	VS033196	0.36	14.15	1.06	3.2	

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm³)
	655.7	656.9	1.2	VS033197	0.15	15.95	0.64	3.2
	656.9	658	1.1	VS033198	0.21	16.00	0.56	3.2
	658	659.3	1.3	VS033199	0.16	15.65	2.20	3.2
	659.3	660.05	0.75	VS033200	0.31	15.25	0.80	3.2
	660.05	660.8	0.75	VS033201	0.44	14.45	1.13	3.2
	660.8	661.65	0.85	VS033202	0.72	14.60	2.00	3.2
	661.65	662.2	0.55	VS033203	0.95	14.30	2.37	3.2
	662.2	663.12	0.92	VS033205	0.80	12.30	2.15	3.82
	663.12	663.9	0.78	VS033206	1.28	10.15	3.20	3.33
	663.9	665.1	1.2	VS033207	0.43	7.60	1.10	3.48
	665.1	665.72	0.62	VS033208	0.16	7.27	0.43	3.31
	665.72	667	1.28	VS033210	0.02	7.59	0.11	2.9
	667	668	1	VS033211	0.04	9.49	0.11	2.9
	668	669	1	VS033212	0.08	8.34	0.21	2.9
	669	669.78	0.78	VS033213	0.04	9.58	0.13	2.9
	669.78	671	1.22	VS033214	0.67	7.74	1.94	2.9
	671	672.3	1.3	VS033215	0.14	8.69	0.28	2.9
	672.3	673.5	1.2	VS033216	0.02	7.42	0.17	2.9
	673.5	674.9	1.4	VS033217	0.02	6.58	0.16	2.9
	674.9	677	2.1	VS033219	0.01	6.57	0.03	2.9
	677	680	3	VS033220	0.01	5.77	0.02	2.9
	680	682.9	2.9	VS033221	0.07	7.79	0.24	2.9
	682.9	684.24	1.34	VS033222	0.01	8.32	0.05	2.9
	684.24	685.14	0.9	VS033223	0.10	9.10	0.29	2.9
	685.14	685.9	0.76	VS033224	0.17	10.85	0.43	2.9
	685.9	687.05	1.15	VS033225	0.01	7.47	0.01	2.9
	687.05	689	1.95	VS033226	0.03	7.73	0.11	2.9
	689	691.18	2.18	VS033227	0.02	8.82	0.08	2.9
	691.18	693.4	2.22	VS033229	0.06	10.70	0.10	2.9
	693.4	695.1	1.7	VS033230	0.11	10.60	0.24	2.9
	695.1	698.1	3	VS033231	0.01	10.05	0.02	2.9
	698.1	699.4	1.3	VS033232	0.00	9.93	0.01	2.9
	699.4	701.6	2.2	VS033233	0.09	8.13	0.23	2.9
VDD23116	434.25	435.78	1.53	VS044413	0.04	10.30	0.06	3.1
	435.78	436.93	1.15	VS044414	0.12	11.50	0.20	2.9
	436.93	437.8	0.87	VS044415	0.05	10.80	0.12	2.9

B zone								
Hole ID	Depth from	Depth to	Sample length	Sample ID	Cu	Fe	Ag	Density
			(m)		(%)	(%)	(g/t)	(g/cm³)
	437.8	438.66	0.86	VS044416	0.11	10.20	0.28	2.9
	438.66	439.44	0.78	VS044417	0.11	17.05	0.24	2.9
	439.44	440.6	1.16	VS044418	0.09	12.35	0.20	2.9
	440.6	441.45	0.85	VS044419	0.03	10.85	0.09	2.9
	441.45	442.8	1.35	VS044420	0.07	9.65	0.12	3.1
	442.8	444.1	1.3	VS044421	0.05	13.75	0.10	3.1
	444.1	445.4	1.3	VS044422	0.02	13.40	0.05	3.1
	445.4	446.65	1.25	VS044423	0.04	11.35	0.11	3.1
	446.65	447.65	1	VS044425	0.01	13.45	0.02	3.1
	447.65	449.8	2.15	VS044426	0.03	15.05	0.03	3.1
	449.8	451.3	1.5	VS044427	0.03	10.05	0.05	3.1
	451.3	452.7	1.4	VS044428	0.03	14.65	0.05	3.1
	452.7	454.08	1.38	VS044429	0.18	10.05	0.38	3.1
	454.08	455.6	1.52	VS044430	0.16	15.00	0.37	3.1
	455.6	457.15	1.55	VS044431	0.05	15.65	0.14	3.1
	457.15	458.75	1.6	VS044432	0.01	13.15	0.24	3.1
	458.75	459.85	1.1	VS044433	0.05	14.10	0.25	3.1
	459.85	461.15	1.3	VS044434	0.01	12.45	0.14	3.1
	461.15	462.4	1.25	VS044435	0.02	14.10	0.14	3.1
	462.4	463.6	1.2	VS044436	0.06	12.25	0.24	3.1
	463.6	464.6	1	VS044437	0.02	16.40	0.11	3.1
	464.6	466.3	1.7	VS044438	0.03	14.30	0.16	3.1
	466.3	468.1	1.8	VS044440	0.10	15.75	0.39	3.1
	468.1	469.16	1.06	VS044441	0.02	14.40	0.11	3.1
	469.16	470.4	1.24	VS044442	0.04	14.40	0.08	3.1
	470.4	471.7	1.3	VS044443	0.27	14.25	0.40	3.1
	471.7	473.3	1.6	VS044444	0.04	15.70	0.07	3.1
	473.3	474.7	1.4	VS044445	0.03	13.30	0.04	3.1
	474.7	476	1.3	VS044446	0.02	14.25	0.03	3.1
	476	477.1	1.1	VS044447	0.02	10.85	0.04	3.1
	477.1	478.5	1.4	VS044448	0.01	14.50	0.04	3.1
	478.5	479.9	1.4	VS044449	0.00	15.25	0.02	3.1
	479.9	481.1	1.2	VS044450	0.15	16.15	0.19	3.1
	481.1	481.9	0.8	VS044451	0.03	12.85	0.04	3.1
	481.9	482.8	0.9	VS044453	0.01	14.30	0.02	3.1
	482.8	483.8	1	VS044454	0.01	16.10	0.14	3.1

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	483.8	485	1.2	VS044455	0.01	15.40	0.02	3.1
	485	486.1	1.1	VS044456	0.09	13.55	0.13	3.1
	486.1	487.4	1.3	VS044457	0.04	15.80	0.04	3.1
	487.4	488.6	1.2	VS044458	0.05	13.55	0.04	3.1
	488.6	489.75	1.15	VS044459	0.04	16.35	0.04	3.1
	489.75	490.9	1.15	VS044460	0.14	11.50	0.19	3.1
	490.9	491.5	0.6	VS044461	0.19	16.10	0.24	3.1
	491.5	492.8	1.3	VS044462	0.11	16.05	0.16	3.1
	492.8	493.9	1.1	VS044463	0.04	15.50	0.06	3.1
	493.9	495.1	1.2	VS044464	0.02	15.95	0.02	3.1
	495.1	496	0.9	VS044465	0.19	18.00	0.14	3.1
	496	496.85	0.85	VS044467	0.04	14.25	0.04	3.1
	496.85	498.1	1.25	VS044468	0.31	15.60	0.36	2.99
	498.1	499.15	1.05	VS044469	0.79	16.70	1.26	3.16
	499.15	500	0.85	VS044470	0.27	14.70	0.35	3.12
	500	501.1	1.1	VS044471	0.26	11.05	0.42	2.91
	501.1	501.84	0.74	VS044472	0.75	16.10	1.38	3.16
	501.84	502.6	0.76	VS044473	1.11	14.60	1.82	3.06
	502.6	503	0.4	VS044474	0.37	14.60	0.62	3.11
	503	503.6	0.6	VS044476	1.07	13.15	1.75	3.12
	503.6	504.35	0.75	VS044477	2.93	14.05	4.81	3.07
	504.35	505.1	0.75	VS044478	2.48	15.80	3.92	3.07
	505.1	506	0.9	VS044479	1.97	18.55	3.07	3.37
	506	507.14	1.14	VS044480	2.61	16.90	4.28	3.26
	507.14	507.95	0.81	VS044481	3.89	14.10	11.55	3.43
	507.95	508.5	0.55	VS044483	5.97	36.40	20.70	4.33
	508.5	509.2	0.7	VS044484	5.96	33.40	9.33	3.92
	509.2	509.95	0.75	VS044485	1.37	15.20	2.90	3.63
	509.95	510.66	0.71	VS044486	3.77	29.10	6.87	3.52
	510.66	511.43	0.77	VS044487	4.99	28.90	8.81	3.42
	511.43	512.1	0.67	VS044488	0.23	5.56	0.53	2.75
	512.1	513.1	1	VS044490	0.01	11.65	0.02	3.1
	513.1	514	0.9	VS044491	0.01	14.80	0.01	3.1
	514	514.8	0.8	VS044492	0.03	11.95	0.02	2.9
	514.8	515.45	0.65	VS044493	0.03	13.60	0.04	2.9
	515.45	516.64	1.19	VS044494	0.01	14.50	0.01	3.1

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	516.64	517.8	1.16	VS044495	0.02	12.10	0.03	3.1
	517.8	519	1.2	VS044496	0.01	12.15	0.02	3.1
	519	520.3	1.3	VS044497	0.02	11.95	0.03	3.1
	520.3	521.3	1	VS044498	0.02	12.35	0.03	3.1
	521.3	522.65	1.35	VS044499	0.10	12.40	0.15	3.1
	522.65	523.65	1	VS044500	0.08	14.40	0.12	3.1
	523.65	524.4	0.75	VS044501	1.21	13.75	2.01	3.1
	524.4	525.3	0.9	VS044502	0.14	12.70	0.21	3.1
	525.3	527.4	2.1	VS044504	0.03	14.65	0.06	3.1
	527.4	528.85	1.45	VS044505	0.10	13.50	0.15	3.1
	528.85	530.5	1.65	VS044506	0.31	14.80	0.55	3.1
	530.5	532.1	1.6	VS044507	0.05	14.40	0.08	3.1
	532.1	533.6	1.5	VS044508	0.03	11.05	0.05	3.1
	533.6	535.2	1.6	VS044509	0.03	12.30	0.04	3.1
	535.2	536.5	1.3	VS044510	0.05	12.80	0.08	3.1
	536.5	538.1	1.6	VS044511	0.19	10.40	0.31	3.1
	538.1	539.6	1.5	VS044512	0.23	12.20	0.51	3.1
	539.6	541.3	1.7	VS044513	0.10	13.35	0.22	3.1
	541.3	543.1	1.8	VS044514	0.11	14.65	0.33	3.1
	543.1	546.1	3	VS044515	0.04	13.10	0.13	3.1
	546.1	549.1	3	VS044516	0.11	14.85	0.22	3.1
	549.1	552.1	3	VS044518	0.20	15.85	0.43	3.1
	552.1	553	0.9	VS044519	0.05	16.20	0.11	3.1
	553	554	1	VS044520	0.55	17.15	1.33	3.1
	554	555.1	1.1	VS044521	1.11	15.80	2.58	3.1
	555.1	556	0.9	VS044522	0.54	17.90	1.19	3.1
	556	557.2	1.2	VS044523	0.17	18.65	0.35	3.1
	557.2	559.4	2.2	VS044524	0.08	14.00	0.20	3.1
	559.4	561	1.6	VS044525	0.04	12.20	0.31	3.1
	561	561.8	0.8	VS044526	0.05	14.15	0.14	3.1
	561.8	563.8	2	VS044528	0.02	10.65	0.06	3.1
	563.8	565	1.2	VS044529	0.02	10.85	0.06	3.1
	565	566.6	1.6	VS044530	0.02	9.83	0.10	3.1
VDD24036	929.6	930.83	1.23	VS049014	0.02	14.70	0.05	3.04
	930.83	932.06	1.23	VS049015	0.02	13.90	0.04	3.05
	932.06	933.29	1.23	VS049017	0.02	14.10	0.04	3.04

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	933.29	934.54	1.25	VS049018	0.01	14.55	0.02	3.06
	934.54	935.77	1.23	VS049019	0.02	14.30	0.05	3.05
	935.77	937.03	1.26	VS049020	0.03	14.90	0.08	3.06
	937.03	938.39	1.36	VS049021	0.09	12.70	0.24	3.03
	938.39	939.75	1.36	VS049022	0.02	14.90	0.04	3.07
	939.75	941.11	1.36	VS049023	0.03	13.60	0.07	2.95
	941.11	942.48	1.37	VS049024	0.02	14.05	0.05	2.92
	942.48	943.63	1.15	VS049025	0.11	14.65	0.27	3.01
	943.63	944.78	1.15	VS049027	0.02	14.75	0.06	3.05
	944.78	945.93	1.15	VS049028	0.11	14.60	0.30	2.92
	945.93	947.08	1.15	VS049029	0.07	14.75	0.16	2.89
	947.08	948.23	1.15	VS049030	0.00	16.25	0.01	3.08
	948.23	949.38	1.15	VS049031	0.01	14.60	0.05	2.99
	949.38	950.53	1.15	VS049032	0.09	16.30	0.22	3.04
	950.53	951.7	1.17	VS049033	0.03	15.10	0.07	3.06
	951.7	952.71	1.01	VS049034	0.14	22.40	0.36	3.59
	952.71	953.72	1.01	VS049036	0.36	27.70	0.94	3.52
	953.72	954.87	1.15	VS049037	0.18	17.15	0.36	3.19
	954.87	956.02	1.15	VS049038	0.17	22.00	0.57	3.2
	956.02	957.17	1.15	VS049039	0.34	24.60	0.47	3.25
	957.17	958.32	1.15	VS049040	0.39	24.90	0.56	3.08
	958.32	959.47	1.15	VS049041	0.15	21.10	0.29	3.24
	959.47	960.62	1.15	VS049043	0.15	22.80	0.37	3.11
	960.62	961.82	1.2	VS049044	0.26	20.20	0.44	3.42
	961.82	962.86	1.04	VS049045	0.04	14.95	0.07	3.12
	962.86	963.9	1.04	VS049046	0.02	14.35	0.03	2.92
	963.9	964.94	1.04	VS049047	0.53	26.80	0.93	3.59
	964.94	966.09	1.15	VS049049	0.01	13.20	0.03	3.01
	966.09	967.24	1.15	VS049050	0.01	13.20	0.01	3.08
	967.24	968.4	1.16	VS049051	0.01	13.20	0.03	3.04
	968.4	969.43	1.03	VS049052	0.01	13.65	0.01	3.04
	969.43	970.46	1.03	VS049053	0.03	14.35	0.04	3.03
	970.46	971.5	1.04	VS049054	0.03	12.60	0.07	3
	971.5	972.7	1.2	VS049055	0.02	13.20	0.05	3
	972.7	973.9	1.2	VS049056	0.01	14.30	0.02	3.09
	973.9	975.1	1.2	VS049057	0.08	14.35	0.19	3.04

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	975.1	976.3	1.2	VS049059	0.07	12.75	0.17	3.05
	976.3	977.5	1.2	VS049060	0.01	13.10	0.03	3
	977.5	978.74	1.24	VS049061	0.02	13.90	0.12	3.04
	978.74	979.62	0.88	VS049062	0.06	14.30	0.14	3.02
	979.62	980.5	0.88	VS049063	0.16	15.50	0.38	3.23
	980.5	981.72	1.22	VS049065	0.04	13.20	0.12	3.03
	981.72	982.94	1.22	VS049066	0.09	13.05	0.27	2.96
	982.94	984.09	1.15	VS049067	0.04	10.25	0.14	2.87
	984.09	985.24	1.15	VS049068	0.07	12.65	0.13	2.77
	985.24	986.4	1.16	VS049069	0.04	10.00	0.10	2.83
	986.4	987.65	1.25	VS049070	0.06	8.65	0.17	2.96
	987.65	988.9	1.25	VS049071	0.01	6.66	0.04	2.92
	988.9	989.92	1.02	VS049072	0.01	9.95	0.05	2.92
	989.92	990.94	1.02	VS049073	0.02	11.10	0.07	2.9
	990.94	991.96	1.02	VS049075	0.03	11.10	0.10	2.88
	991.96	993	1.04	VS049076	0.07	12.70	0.19	2.97
	993	994.28	1.28	VS049077	0.02	12.15	0.03	2.93
	994.28	995.56	1.28	VS049078	0.03	12.70	0.04	2.95
	995.56	996.84	1.28	VS049079	0.01	12.30	0.03	2.99
	996.84	998.12	1.28	VS049080	0.01	11.65	0.04	2.95
	998.12	999.41	1.29	VS049081	0.06	10.00	0.13	2.93
	999.41	1000.51	1.1	VS049082	0.21	24.20	0.73	3.26
	1000.51	1001.62	1.11	VS049083	0.20	17.95	0.78	3.29
	1001.62	1002.7	1.08	VS049085	0.11	16.40	0.35	2.99
	1002.7	1003.82	1.12	VS049086	0.43	23.60	1.26	3.57
	1003.82	1005.05	1.23	VS049088	0.04	12.70	0.10	2.93
	1005.05	1006.28	1.23	VS049089	0.00	10.25	0.01	2.87
	1006.28	1007.52	1.24	VS049090	0.00	11.00	0.01	2.88
	1007.52	1008.75	1.23	VS049091	0.01	8.70	0.03	2.74
	1008.75	1009.98	1.23	VS049092	0.10	11.90	0.27	2.91
	1009.98	1011.23	1.25	VS049093	0.00	12.45	0.01	2.88
	1011.23	1012.44	1.21	VS049094	0.00	13.70	0.01	2.98
	1012.44	1013.67	1.23	VS049095	0.02	13.95	0.04	3.11
	1013.67	1014.9	1.23	VS049096	0.00	12.75	0.03	3.16
	1014.9	1016.13	1.23	VS049098	0.00	11.75	0.03	2.97
	1016.13	1017.4	1.27	VS049099	0.00	10.95	0.02	2.93

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	1017.4	1019.06	1.66	VS049100	0.01	13.55	0.05	3.09
	1019.06	1020.72	1.66	VS049101	0.00	12.35	0.01	3.02
	1020.72	1022.38	1.66	VS049102	0.00	10.85	0.01	2.92
	1022.38	1024.04	1.66	VS049103	0.01	11.65	0.05	2.98
	1024.04	1026.09	2.05	VS049104	0.00	11.90	0.01	3
	1026.09	1028.14	2.05	VS049105	0.00	12.55	0.01	3
	1028.14	1030.2	2.06	VS049106	0.00	10.55	0.03	3
	1030.2	1030.7	0.5	CORELOSS	0.00	0.00	0.00	3
	1030.7	1032.83	2.13	VS049108	0.01	11.60	0.04	3
	1032.83	1034.94	2.11	VS049109	0.00	11.50	0.05	3
	1034.94	1037.1	2.16	VS049110	0.07	10.45	0.38	3
VDD24057	555.36	556.36	1	VS054558	0.16	9.93	0.10	2.84
	556.36	557.59	1.23	VS054559	0.56	18.55	0.51	3.08
	557.59	558.76	1.17	VS054560	0.46	17.80	0.47	3.4
	558.76	559.9	1.14	VS054561	0.12	14.55	0.14	3.02
	559.9	560.72	0.82	VS054563	0.35	15.60	0.45	2.91
	560.72	561.5	0.78	VS054564	1.48	15.90	1.86	3.09
	561.5	562.3	0.8	VS054565	1.18	20.10	1.40	3.33
	562.3	563.11	0.81	VS054566	0.73	11.40	0.74	2.95
	563.11	564.26	1.15	VS054567	0.07	15.80	0.04	2.95
	564.26	565.41	1.15	VS054568	0.04	17.70	0.03	3.08
	565.41	566.56	1.15	VS054569	0.03	13.65	0.03	2.96
	566.56	567.71	1.15	VS054570	0.05	15.95	0.05	3.07
	567.71	568.86	1.15	VS054571	0.05	18.95	0.05	3.16
	568.86	570.01	1.15	VS054573	0.07	15.25	0.06	3.04
	570.01	571.16	1.15	VS054574	0.07	15.75	0.06	2.98
	571.16	572.41	1.25	VS054575	0.10	17.05	0.10	3.21
	572.41	573.11	0.7	VS054576	0.59	16.95	0.51	3.16
	573.11	573.8	0.69	VS054577	0.25	16.30	0.22	3.22
	573.8	574.6	0.8	VS054578	0.18	12.70	0.17	2.92
	574.6	575.32	0.72	VS054579	0.23	12.15	0.18	2.9
575.32	576.52	1.2	VS054580	0.13	14.15	0.09	3.12	
576.52	577.72	1.2	VS054581	0.13	13.20	0.13	3.07	
577.72	578.92	1.2	VS054583	0.08	15.10	0.07	3.09	
578.92	580.17	1.25	VS054584	0.14	16.00	0.54	3.08	
580.17	581.46	1.29	VS054585	1.19	17.45	3.13	3.16	

B zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm³)
	581.46	582.76	1.3	VS054586	1.03	10.35	2.97	4.86
	582.76	583.6	0.84	VS054588	1.25	58.40	1.58	2.87
	583.6	584.52	0.92	VS054589	0.91	20.90	1.60	3.27
	584.52	585.53	1.01	VS054590	0.39	16.25	0.76	3.01

ABBA zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm³)
VDD0127B	964.25	965.17	0.92	VS053252	0.40	16.30	0.60	3.31
	965.17	966.1	0.93	VS053253	0.64	16.55	0.84	3.13
	966.1	967	0.9	VS053254	0.27	17.90	0.34	3.16
	967	968.28	1.28	VS053255	0.31	15.30	0.36	2.97
	968.28	969.56	1.28	VS053256	0.07	16.15	0.08	3.05
	969.56	970.85	1.29	VS053257	0.13	14.50	0.21	2.94
	970.85	972.02	1.17	VS053258	0.66	14.60	0.90	3.06
	972.02	973.19	1.17	VS053259	0.45	16.00	0.65	3.14
	973.19	974.3	1.11	VS053260	0.44	17.20	0.62	3.22
	974.3	975.55	1.25	VS053262	0.42	17.05	0.59	3.27
	975.55	976.85	1.3	VS053263	0.04	14.55	0.06	3.07
	976.85	978.05	1.2	VS053264	0.02	15.35	0.02	3.02
	978.05	979.27	1.22	VS053265	0.11	16.45	0.13	3
	979.27	980.55	1.28	VS053266	0.12	13.00	0.17	2.95
	980.55	981.45	0.9	VS053267	0.11	10.85	0.12	2.99
	981.45	982.3	0.85	VS053268	0.39	10.40	0.43	2.91
	982.3	983.27	0.97	VS053269	0.08	10.75	0.12	2.9
	983.27	984.49	1.22	VS053270	0.35	18.80	0.65	3.22
	984.49	985.76	1.27	VS053272	0.14	13.10	0.18	2.91
	985.76	987.03	1.27	VS053273	0.06	13.10	0.09	3.07
	987.03	988.15	1.12	VS053274	0.09	11.20	0.10	2.9
	988.15	989.22	1.07	VS053275	0.26	15.35	0.32	3.18
	989.22	990.32	1.1	VS053276	0.16	19.70	0.40	3.53
990.32	991.42	1.1	VS053277	0.31	20.10	0.57	3.23	
991.42	992.42	1	VS053278	0.57	14.35	1.01	3.11	
992.42	993.6	1.18	VS053279	0.62	12.70	1.13	3.29	
993.6	994.15	0.55	VS053280	7.15	38.60	14.80	4.54	
994.15	994.9	0.75	VS053282	5.40	31.40	11.20	3.96	

ABBA zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	994.9	996.03	1.13	VS053283	0.74	11.40	1.27	3.02
	996.03	997	0.97	VS053284	0.75	21.90	1.05	3.03
	997	998.2	1.2	VS053285	0.32	19.70	0.63	3.34
	998.2	998.8	0.6	VS053286	0.98	40.10	2.12	3.61
	998.8	1000.1	1.3	VS053288	0.03	11.20	0.06	3.02
	1000.1	1001.4	1.3	VS053289	0.01	11.30	0.03	2.98
	1001.4	1002.7	1.3	VS053290	0.01	9.75	0.03	2.93
	1002.7	1004	1.3	VS053291	0.02	9.35	0.08	2.95
	1004	1005.3	1.3	VS053292	0.02	11.60	0.04	3.05
	1005.3	1006.6	1.3	VS053293	0.02	10.95	0.04	3.14
	1006.6	1007.9	1.3	VS053294	0.02	11.00	0.03	3.05
	1007.9	1008.97	1.07	VS053295	0.01	7.49	0.01	2.89
	1008.97	1009.95	0.98	VS053296	0.03	11.40	0.08	3.36
	1009.95	1010.55	0.6	VS053298	0.09	54.80	0.24	4.11
	1010.55	1011.6	1.05	VS053299	0.08	10.80	0.12	3.29
	1011.6	1012.46	0.86	VS053300	0.03	10.40	0.12	2.94
	1012.46	1013.2	0.74	VS053301	0.02	11.50	0.06	3.08
	1013.2	1014.25	1.05	VS053302	0.02	11.40	0.06	2.94
	1014.25	1015.53	1.28	VS053564	0.02	12.75	0.04	3.09
	1015.53	1016.74	1.21	VS053565	0.02	13.20	0.04	3.09
	1016.74	1018.04	1.3	VS053566	0.05	12.10	0.07	3
	1018.04	1019.27	1.23	VS053567	0.09	12.70	0.09	3
	1019.27	1020.57	1.3	VS053568	0.09	14.50	0.10	3.11
	1020.57	1021.78	1.21	VS053569	0.05	14.25	0.10	3.27
	1021.78	1023.07	1.29	VS053570	0.01	13.05	0.03	3.11
	1023.07	1024.33	1.26	VS053571	0.02	13.45	0.05	3.02
	1024.33	1025.55	1.22	VS053572	0.04	12.45	0.03	3.04
	1025.55	1026.85	1.3	VS053574	0.04	14.65	0.09	2.93
	1026.85	1028.15	1.3	VS053575	0.02	13.90	0.02	3
	1028.15	1029.43	1.28	VS053576	0.13	11.65	0.32	2.91
	1029.43	1029.74	0.31	VS053577	3.45	46.20	8.82	4.52
	1029.74	1030.58	0.84	VS053578	1.89	28.30	4.64	3.92
	1030.58	1031.9	1.32	VS053580	0.03	11.25	0.07	3.06
	1031.9	1033.2	1.3	VS053581	0.01	12.80	0.05	3.03
	1033.2	1034.5	1.3	VS053582	0.03	12.80	0.05	2.97
	1034.5	1035.8	1.3	VS053583	0.02	13.10	0.03	3.12

ABBA zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	1035.8	1037.1	1.3	VS053584	0.02	12.80	0.04	3.09
	1037.1	1038.4	1.3	VS053585	0.05	11.80	0.11	3.03
	1038.4	1039.7	1.3	VS053586	0.02	10.05	0.05	2.96
	1039.7	1041	1.3	VS053587	0.01	11.80	0.05	2.98
	1041	1042.3	1.3	VS053588	0.01	11.95	0.04	2.95
	1042.3	1043.6	1.3	VS053590	0.01	12.15	0.02	3.01
	1043.6	1044.8	1.2	VS053591	0.00	11.15	0.05	2.87
	1044.8	1045.96	1.16	VS053592	0.02	9.78	0.10	2.83
	1045.96	1047.12	1.16	VS053593	0.03	10.25	0.07	2.79
	1047.12	1047.92	0.8	VS053594	0.05	13.45	0.10	3.18
	1047.92	1048.8	0.88	VS053595	0.21	12.10	0.51	3
	1048.8	1049.6	0.8	VS053596	3.11	20.80	8.97	3.39
	1049.6	1050.28	0.68	VS053597	3.98	24.60	11.20	3.44
	1050.28	1051.08	0.8	VS053599	3.89	24.70	10.90	4.24
	1167.6	1168.4	0.8	VS052218	0.13	17.80	0.12	3.52
	1168.4	1169.15	0.75	VS052219	0.36	17.70	0.45	3.22
	1169.15	1169.75	0.6	VS052221	0.81	18.65	0.95	3.37
	1169.75	1170.9	1.15	VS052222	0.21	17.95	0.26	3.21
	1170.9	1171.95	1.05	VS052223	0.19	15.30	0.30	2.98
	1171.95	1173.05	1.1	VS052224	0.39	15.10	0.53	3.04
	1173.05	1174.3	1.25	VS052225	0.42	17.20	0.56	3.15
	1174.3	1175.45	1.15	VS052226	0.33	18.15	0.46	3.11
	1175.45	1176.75	1.3	VS052228	0.25	16.75	0.32	3.18
	1176.75	1177.95	1.2	VS052229	0.29	16.35	0.42	3.11
	1177.95	1179.25	1.3	VS052230	0.30	15.95	0.41	3.09
VDD24043B	1179.25	1180.55	1.3	VS052231	0.84	16.05	1.22	3.12
	1180.55	1181.85	1.3	VS052232	0.62	15.35	0.96	3.18
	1181.85	1183.15	1.3	VS052233	0.12	15.40	0.19	3.09
	1183.15	1184.35	1.2	VS052235	0.34	15.85	0.59	3.03
	1184.35	1185.4	1.05	VS052236	0.01	14.85	0.01	3.26
	1185.4	1186.5	1.1	VS052237	0.06	16.40	0.10	3.08
	1186.5	1187.7	1.2	VS052238	0.10	15.80	0.16	3.12
	1187.7	1188.8	1.1	VS052239	0.01	15.25	0.01	3.03
	1188.8	1189.95	1.15	VS052240	0.50	17.30	0.77	3.03
	1189.95	1191.1	1.15	VS052242	0.07	15.40	0.10	3.01
	1191.1	1192.1	1	VS052243	0.04	15.60	0.06	3.05

ABBA zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	1192.1	1193.15	1.05	VS052244	0.02	15.80	0.01	2.96
	1193.15	1194.3	1.15	VS052245	0.04	16.05	0.07	3.12
	1194.3	1195.6	1.3	VS052246	0.01	13.70	0.03	3.15
	1195.6	1196.9	1.3	VS052247	0.03	12.80	0.03	3.06
	1196.9	1198.2	1.3	VS052248	0.12	14.55	0.20	3.26
	1198.2	1199.5	1.3	VS052249	1.31	14.55	2.83	3.28
	1199.5	1200.15	0.65	VS052251	4.44	26.30	11.85	3.74
	1200.15	1201.15	1	VS052252	0.86	25.60	1.70	3.12
	1201.15	1201.8	0.65	VS052253	0.89	14.50	1.55	3.24
	1201.8	1202.9	1.1	VS052254	0.68	22.40	1.16	4.33
	1202.9	1204.05	1.15	VS052255	1.01	15.00	1.65	3.3
	1204.05	1205.15	1.1	VS052256	1.06	11.55	1.96	2.93
	1205.15	1206.35	1.2	VS052257	0.34	16.20	0.58	3.2
	1206.35	1207.3	0.95	VS052259	0.89	14.65	1.55	3.15
	1207.3	1208.6	1.3	VS052260	1.01	20.50	1.77	3.6
	1208.6	1209.6	1	VS052261	0.48	12.95	0.83	3.21
	1209.6	1210.9	1.3	VS052262	0.37	14.30	0.62	3.47
	1210.9	1212.2	1.3	VS052263	0.68	23.50	1.22	4.82
	1212.2	1213.5	1.3	VS052264	1.14	19.35	2.02	3.42
	1213.5	1214.75	1.25	VS052265	0.86	25.20	1.54	3.78
	1214.75	1215.85	1.1	VS052266	0.69	14.35	1.24	3.34
	1215.85	1217.05	1.2	VS052267	0.93	14.75	1.87	3.49
	1217.05	1218	0.95	VS052269	0.80	24.90	1.60	3.54
	1218	1218.75	0.75	VS052270	0.43	24.60	0.71	3.78
	1218.75	1219.8	1.05	VS052271	0.06	14.70	0.08	3.07
	1219.8	1221.1	1.3	VS052272	0.01	14.75	0.02	3.04
	1221.1	1222.15	1.05	VS052273	0.02	14.95	0.03	2.95
	1222.15	1223.4	1.25	VS052274	0.02	15.75	0.02	2.99
	1223.4	1224.7	1.3	VS052275	0.02	15.15	0.03	3.07
	1224.7	1225.55	0.85	VS052276	0.04	16.20	0.05	3.08
	1225.55	1226.65	1.1	VS052277	0.04	13.90	0.02	3
	1226.65	1227.8	1.15	VS052279	0.01	15.90	0.01	3.3
	1227.8	1228.9	1.1	VS052280	0.01	15.75	0.01	3.23
	1228.9	1230.1	1.2	VS052281	0.02	14.85	0.02	3.05
	1230.1	1231	0.9	VS052282	0.01	14.85	0.02	3.05
	1231	1232	1	VS052283	0.02	17.30	0.02	3.38

ABBA zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	1232	1233.1	1.1	VS052284	0.03	16.80	0.01	3.24
	1233.1	1234.35	1.25	VS052285	0.01	15.20	0.01	3.13
	1234.35	1235.4	1.05	VS052286	0.02	13.85	0.03	3.25
	1235.4	1236.45	1.05	VS052287	0.06	9.07	0.12	3
	1236.45	1237	0.55	VS052288	0.07	14.50	0.09	3.34
	1237	1237.9	0.9	VS052289	0.04	14.95	0.07	3.33
	1237.9	1238.85	0.95	VS052291	0.07	15.50	0.09	3.46
	1238.85	1240.05	1.2	VS052292	0.02	14.30	0.03	3.36
	1240.05	1241.1	1.05	VS052293	0.08	14.20	0.10	3.05
	1241.1	1242.1	1	VS052294	0.05	12.25	0.06	2.99
	1242.1	1243.2	1.1	VS052295	0.03	8.97	0.07	2.99
	1243.2	1244.2	1	VS052296	0.02	13.20	0.09	3.07
	1244.2	1245.1	0.9	VS052297	0.16	16.35	0.42	3.19
	1245.1	1246.35	1.25	VS052299	0.18	30.30	0.80	3.92
	1246.35	1247.15	0.8	VS052300	0.30	23.00	1.13	4.11
	1247.15	1248.35	1.2	VS052301	0.07	17.35	0.20	3.17
	1248.35	1249.35	1	VS052302	0.50	18.00	1.42	3.5
	1249.35	1250.45	1.1	VS052303	0.47	13.70	1.37	3.15
	1250.45	1251.65	1.2	VS052304	0.94	17.75	2.38	3.46
	1251.65	1252.5	0.85	VS052306	0.29	16.65	0.86	3.36
	1252.5	1253.4	0.9	VS052307	0.26	15.10	0.23	3.14
	1253.4	1254.4	1	VS052308	0.17	16.75	0.42	3.41
	1254.4	1255.5	1.1	VS052309	0.77	26.00	1.94	4.27
	1255.5	1256.4	0.9	VS052311	0.32	10.05	0.96	3.04
	1256.4	1256.95	0.55	VS052312	0.15	11.95	0.51	3.4
	1256.95	1258.15	1.2	VS052313	0.90	11.40	4.31	2.94
	1258.15	1259.4	1.25	VS052315	2.09	22.00	7.00	3.16
	1259.4	1260.7	1.3	VS052316	0.55	15.90	1.88	3.34
VDD24043C	1153.05	1153.8	0.75	VS054049	0.97	10.40	2.65	3.1
	1153.8	1154.65	0.85	VS054050	2.35	12.60	5.79	3.3
	1154.65	1155.95	1.3	VS054051	0.12	11.10	0.30	3.1
	1155.95	1157.25	1.3	VS054052	0.08	10.15	0.21	3.02
	1157.25	1158.55	1.3	VS054053	0.46	11.25	1.24	3.1
	1158.55	1159.75	1.2	VS054054	0.12	9.13	0.31	3.1
	1159.75	1161	1.25	VS054055	0.12	9.03	0.28	3.1
	1161	1162.1	1.1	VS054056	0.19	9.74	0.56	3.28

ABBA zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	1162.1	1163	0.9	VS054057	0.10	9.95	0.34	3.1
	1163	1163.7	0.7	VS054059	0.04	10.95	0.13	3.1
	1163.7	1164.6	0.9	VS054060	0.04	5.32	0.15	2.66
	1164.6	1165.6	1	VS054061	0.03	7.63	0.12	2.85
	1165.6	1166.85	1.25	VS054062	0.14	5.74	0.34	2.71
	1166.85	1167.9	1.05	VS054063	0.01	5.40	0.06	2.71
	1167.9	1168.55	0.65	VS054064	0.01	1.78	0.08	3
	1168.55	1169.45	0.9	VS054065	0.00	1.92	0.03	3
	1169.45	1170.6	1.15	VS054066	0.00	6.63	0.03	3
	1170.6	1171.9	1.3	VS054067	0.00	5.98	0.01	3
	1171.9	1173.1	1.2	VS054069	0.00	5.81	0.01	3
	1173.1	1173.9	0.8	VS054070	0.00	6.57	0.01	2.92
	1173.9	1174.65	0.75	VS054071	0.00	6.01	0.01	3
	1174.65	1175.7	1.05	VS054072	0.03	13.20	0.07	3.09
	1175.7	1176.85	1.15	VS054073	0.03	8.43	0.05	2.76
	1176.85	1177.95	1.1	VS054074	0.00	10.15	0.01	3
	1177.95	1179.2	1.25	VS054075	0.05	9.72	0.13	3.1
	1179.2	1179.9	0.7	VS054076	0.00	7.78	0.02	3
	1179.9	1180.65	0.75	VS054077	0.15	9.38	0.57	2.84
	1180.65	1181.35	0.7	VS054079	0.71	12.35	1.34	2.85
	1181.35	1182.45	1.1	VS054080	0.13	13.70	0.47	3
	1182.45	1183.45	1	VS054081	0.04	12.55	0.12	3.16
	1183.45	1184.55	1.1	VS054082	0.06	14.45	0.17	3
	1184.55	1185.75	1.2	VS054083	0.02	14.80	0.03	3.07
	1185.75	1186.95	1.2	VS054084	0.01	10.35	0.01	3
	1186.95	1188.15	1.2	VS054085	0.05	10.40	0.08	3
	1188.15	1189.2	1.05	VS054086	0.09	9.32	0.12	2.9
	1189.2	1190.5	1.3	VS054087	0.01	9.13	0.07	2.94
	1190.5	1191.75	1.25	VS054088	0.01	10.50	0.04	3
	1191.75	1192.7	0.95	VS054089	0.06	10.10	0.09	3.03
	1192.7	1195.6	2.9	VS054352	0.02	9.38	0.07	3
	1195.6	1196.75	1.15	VS054353	0.03	14.90	0.08	3.34
	1196.75	1198.1	1.35	VS054354	0.01	10.90	0.03	3.26
	1198.1	1199.2	1.1	VS054355	0.04	15.80	0.04	3.1
	1199.2	1200.65	1.45	VS054356	0.01	15.05	0.01	3.18
	1200.65	1201.6	0.95	VS054357	0.00	11.35	0.01	3.1

ABBA zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	1201.6	1202.2	0.6	VS054359	0.05	15.70	0.10	3.1
	1202.2	1203.55	1.35	VS054360	0.01	14.35	0.01	2.96
	1203.55	1204.8	1.25	VS054361	0.01	17.45	0.02	3.1
	1204.8	1206.1	1.3	VS054362	0.00	15.70	0.01	3.07
	1206.1	1207.5	1.4	VS054363	0.07	16.40	0.15	3.12
	1207.5	1208	0.5	VS054364	0.02	15.15	0.01	3.1
	1208	1208.9	0.9	VS054366	0.38	15.85	0.95	2.97
	1208.9	1209.9	1	VS054367	0.23	15.70	0.53	3.05
	1209.9	1210.95	1.05	VS054368	0.60	16.85	1.47	3.07
	1210.95	1211.6	0.65	VS054369	0.55	16.75	1.39	3.1
	1211.6	1212.1	0.5	VS054370	3.65	19.45	8.88	3.22
	1212.1	1213.3	1.2	VS054371	0.01	14.10	0.05	3.1
	1213.3	1214.3	1	VS054372	0.02	14.85	0.04	3.08
	1214.3	1215.7	1.4	VS054373	0.03	15.55	0.04	3.1
	1215.7	1216.25	0.55	VS054374	0.02	14.50	0.03	3.1
	1216.25	1216.75	0.5	VS054376	0.25	12.95	0.55	3.04
	1216.75	1217.65	0.9	VS054377	0.66	18.50	1.53	3.14
	1217.65	1218.8	1.15	VS054378	0.13	18.40	0.34	3.22
	1218.8	1219.5	0.7	VS054379	0.83	17.30	1.94	3.13
	1219.5	1220.45	0.95	VS054380	0.72	18.40	1.71	3.26
	1220.45	1221.25	0.8	VS054382	0.23	16.05	0.56	3.1
	1221.25	1222.5	1.25	VS054383	0.02	13.95	0.05	3.1
	1222.5	1223.35	0.85	VS054384	0.06	13.90	0.16	3.23
	1223.35	1223.8	0.45	VS054385	0.14	13.70	0.25	2.96
	1223.8	1224.7	0.9	VS054386	0.22	17.60	0.41	3.12
	1224.7	1226.05	1.35	VS054387	0.19	19.00	0.48	3.21
	1226.05	1226.5	0.45	VS054388	0.58	15.30	1.24	2.94
	1226.5	1227.65	1.15	VS054389	0.21	14.00	0.37	3.08
	1227.65	1228.7	1.05	VS054390	0.37	17.85	0.84	2.99
	1228.7	1229.45	0.75	VS054391	0.41	18.30	0.86	3.18
	1229.45	1230.8	1.35	VS054393	0.15	18.35	0.31	3.12
	1230.8	1231.65	0.85	VS054394	0.30	19.05	0.55	3.23
	1231.65	1232.8	1.15	VS054395	0.51	18.20	1.11	3.15
	1232.8	1233.4	0.6	VS054396	0.47	20.00	1.08	3.2
	1233.4	1234.9	1.5	VS054397	0.55	18.75	1.18	3.18
	1234.9	1235.2	0.3	VS054398	0.41	17.10	0.88	3.07

ABBA zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	1235.2	1236.35	1.15	VS054399	0.44	18.65	1.01	3.27
	1236.35	1237.6	1.25	VS054400	1.91	18.35	4.56	3.31
	1237.6	1238.3	0.7	VS054401	0.96	18.50	2.22	3.15
	1238.3	1239.05	0.75	VS054403	1.44	19.00	3.40	3.16
	1239.05	1240.25	1.2	VS054404	0.71	18.40	1.82	3.26
	1240.25	1241.43	1.18	VS054405	0.72	18.85	1.53	3.16
	1241.43	1242.4	0.97	VS054406	0.62	19.60	1.36	3.16
	1242.4	1243.35	0.95	VS054407	0.33	14.80	0.81	3.12
	1243.35	1244.5	1.15	VS054408	1.35	18.70	3.26	3.1
	1244.5	1245.75	1.25	VS054410	0.19	17.25	0.49	3.12
	1245.75	1246.1	0.35	VS054411	0.44	17.25	1.10	3.07
	1246.1	1246.6	0.5	VS054412	0.63	13.80	1.33	2.99
	1246.6	1247.8	1.2	VS054413	0.30	16.95	0.65	3.18
	1247.8	1250.55	2.75	VS054414	0.08	15.20	0.17	3.07
	1250.55	1253.3	2.75	VS054415	0.05	14.25	0.09	3.1
	1253.3	1256.05	2.75	VS054416	0.07	15.95	0.14	3.1
	1256.05	1257.35	1.3	VS054417	0.03	15.35	0.04	3.1
	1257.35	1258.6	1.25	VS054418	0.06	15.40	0.10	3.1
	1258.6	1259.85	1.25	VS054420	0.02	17.25	0.05	3.1
	1259.85	1260.9	1.05	VS054421	0.02	15.90	0.02	3.1
	1260.9	1261.8	0.9	VS054422	0.06	15.65	0.12	3.07
	1261.8	1262.3	0.5	VS054423	0.02	17.40	0.02	3.1
	1262.3	1263.25	0.95	VS054424	0.14	18.35	0.31	3.1
	1263.25	1264.2	0.95	VS054425	0.60	16.75	1.22	3.1
	1264.2	1265.25	1.05	VS054426	0.07	15.55	0.10	3.1
	1265.25	1266.25	1	VS054427	0.02	14.40	0.03	3.1
	1266.25	1267.35	1.1	VS054429	0.09	16.95	0.13	3.22
	1267.35	1268.55	1.2	VS054430	0.41	19.70	0.68	3.25
	1268.55	1269.65	1.1	VS054431	0.31	16.45	0.64	2.99
	1269.65	1270.95	1.3	VS054432	0.13	17.00	0.30	3.4
	1270.95	1272.2	1.25	VS054433	0.60	18.65	1.36	3.27
	1272.2	1273.45	1.25	VS054434	0.34	18.70	0.78	3.29
	1273.45	1274.7	1.25	VS054435	0.16	16.45	0.29	3.05
	1274.7	1275.95	1.25	VS054436	0.24	16.95	0.43	3.26
	1275.95	1277.1	1.15	VS054437	0.23	16.30	0.52	3.24
	1277.1	1278.1	1	VS054439	0.25	17.75	0.50	3.13

ABBA zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	1278.1	1278.95	0.85	VS054440	1.30	20.80	2.52	3.21
	1278.95	1280.2	1.25	VS054441	0.16	16.50	0.33	3.03
	1280.2	1281.35	1.15	VS054442	0.32	16.45	0.66	3.13
	1281.35	1282.5	1.15	VS054443	0.09	17.25	0.18	3.16
	1282.5	1283.55	1.05	VS054444	0.31	16.30	0.61	3.06
	1283.55	1284.4	0.85	VS054445	0.56	17.00	1.26	3.23
	1284.4	1285.25	0.85	VS054446	0.10	13.50	0.21	2.99
	1285.25	1286.05	0.8	VS054447	1.54	10.60	3.10	2.97
	1286.05	1287.2	1.15	VS054448	0.74	16.00	1.78	3.17
	1287.2	1288.5	1.3	VS054450	0.41	15.05	0.93	3.34
	1288.5	1289.75	1.25	VS054451	0.39	14.50	0.87	3.12
	1289.75	1291	1.25	VS054452	0.52	14.80	1.15	3.1
	1291	1292.1	1.1	VS054453	0.58	14.25	1.36	3.2
	1292.1	1293	0.9	VS054454	0.56	13.50	1.23	3.29
	1293	1294.3	1.3	VS054455	0.03	14.70	0.07	3.24
	1294.3	1295.45	1.15	VS054456	0.02	15.75	0.03	2.97
	1295.45	1296.7	1.25	VS054457	0.01	12.25	0.01	3.08
	1296.7	1297.9	1.2	VS054458	0.01	10.70	0.01	3.09
	1297.9	1299.2	1.3	VS054459	0.06	10.20	0.07	3.02
	1299.2	1299.9	0.7	VS054460	0.05	10.75	0.08	3.1
	1299.9	1300.45	0.55	VS054462	0.14	16.10	0.23	3.15
	1300.45	1301	0.55	VS054463	1.18	33.80	2.76	4.17
	1301	1302	1	VS054464	1.03	33.00	1.67	3.86

2.4 A-zone

A zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	916.6	918.35	1.75	VS051917	0.01	8.80	0.06	3
VDD24043B	918.35	920	1.65	VS051918	0.00	8.39	0.02	3.09
	920	921.5	1.5	VS051919	0.01	8.49	0.02	3
	921.5	923	1.5	VS051920	0.04	8.55	0.06	2.85

A zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	923	923.95	0.95	VS051921	0.21	6.45	0.38	2.77
	923.95	924.8	0.85	VS051922	0.13	6.86	0.29	2.82
	924.8	926.4	1.6	VS051923	0.03	7.57	0.08	2.83
	926.4	929	2.6	VS051924	0.03	8.70	0.04	2.9
	929	930.9	1.9	VS051925	0.04	9.33	0.07	3
	930.9	932.9	2	VS051926	0.36	9.04	0.60	3
	932.9	934.25	1.35	VS051928	0.31	9.84	0.54	2.92
	934.25	935.25	1	VS051929	0.33	7.73	0.62	2.81
	935.25	937.75	2.5	VS051930	0.09	10.10	0.17	3
	937.75	940	2.25	VS051931	0.05	10.00	0.10	2.91
	940	942.45	2.45	VS051932	0.04	10.05	0.09	3
	942.45	944.2	1.75	VS051933	0.14	9.51	0.20	2.84
	944.2	945.85	1.65	VS051934	0.99	12.20	1.88	3.09
	945.85	948.75	2.9	VS051935	0.10	9.74	0.12	3.18
	948.75	951	2.25	VS051936	0.06	9.31	0.05	2.98
	951	953.7	2.7	VS051937	0.06	9.33	0.06	3.03
	953.7	956.15	2.45	VS051939	0.06	9.54	0.10	3.05
	956.15	957.9	1.75	VS051940	0.04	9.57	0.10	3.01
	957.9	960.6	2.7	VS051941	0.02	9.36	0.06	3
	960.6	963.3	2.7	VS051942	0.04	9.57	0.08	3.02
	963.3	965.9	2.6	VS051943	0.03	10.05	0.05	3
	965.9	968.2	2.3	VS051944	0.02	10.10	0.04	3
	968.2	970	1.8	VS051945	0.05	10.05	0.05	3
	970	972	2	VS051946	0.08	10.05	0.05	3
	972	974.2	2.2	VS051947	0.10	9.58	0.10	3
	974.2	976.6	2.4	VS051948	0.06	10.20	0.07	3
	976.6	978.6	2	VS051950	0.06	10.30	0.05	3
	978.6	979.67	1.07	VS051951	0.01	9.85	0.05	3
	979.67	980.75	1.08	VS051952	0.03	13.05	0.06	3.01
	980.75	982.05	1.3	VS051954	0.36	11.40	0.40	3
	982.05	983.15	1.1	VS051955	4.78	30.80	6.76	3.08
	983.15	983.8	0.65	VS051956	0.77	16.20	0.99	3
	983.8	984.73	0.93	VS051957	0.49	8.44	0.69	2.74
	984.73	985.3	0.57	VS051958	0.29	9.90	0.38	2.72
	985.3	986.2	0.9	VS051959	0.82	6.63	0.88	2.75
	986.2	986.65	0.45	VS051960	0.27	6.15	0.22	3

A zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	986.65	987.6	0.95	VS051961	0.03	4.59	0.01	3
	987.6	988.99	1.39	VS051962	0.02	2.74	0.01	3
	988.99	990.25	1.26	VS051963	0.11	2.86	0.22	2.71
	990.25	991.15	0.9	VS051965	0.16	4.84	0.34	3
	991.15	992.25	1.1	VS051966	0.08	9.16	0.20	3
	992.25	993.4	1.15	VS051967	0.07	11.85	0.16	3
	993.4	993.7	0.3	VS051968	0.05	16.10	0.15	3
	993.7	994.7	1	VS051969	0.01	9.38	0.02	3
	994.7	995.7	1	VS051970	0.00	8.49	0.01	3
	995.7	997	1.3	VS051971	0.01	9.49	0.03	3
	997	998.2	1.2	VS051972	0.05	13.95	0.12	3.17
	998.2	999.4	1.2	VS051973	0.06	15.00	0.17	3
	999.4	1000.55	1.15	VS051974	0.05	15.05	0.15	3
	1000.55	1001.99	1.44	VS051976	0.04	10.75	0.10	3
	1001.99	1003.35	1.36	VS051977	0.01	11.90	0.04	3
	1003.35	1005.05	1.7	VS051978	0.03	16.55	0.10	3
	1005.05	1006.75	1.7	VS051979	0.05	14.70	0.14	3.15
	1006.75	1008.75	2	VS051980	0.20	20.10	0.45	3.1
	1008.75	1011	2.25	VS051981	0.05	13.90	0.18	3.02
	1011	1013.28	2.28	VS051982	0.06	9.51	0.18	3.1
	1013.28	1015.62	2.34	VS051983	0.02	9.06	0.09	3.1
	1015.62	1018	2.38	VS051984	0.03	8.69	0.10	3.1
	1018	1020.35	2.35	VS051985	0.04	11.55	0.13	3.1
	1020.35	1022.55	2.2	VS051987	0.05	10.20	0.16	3.13
	1022.55	1023.9	1.35	VS051988	0.03	9.41	0.09	3.1
	1023.9	1025.2	1.3	VS051989	0.04	9.59	0.19	3.1
	1025.2	1026.5	1.3	VS051990	0.10	13.90	0.38	3.1
	1026.5	1027.65	1.15	VS051991	0.04	10.20	0.21	3.1
	1027.65	1029	1.35	VS051992	0.02	11.15	0.09	3.1
	1029	1030.2	1.2	VS051993	0.02	11.25	0.07	3.06
	1030.2	1031.5	1.3	VS051995	0.01	10.15	0.04	3.1
	1031.5	1033	1.5	VS051996	0.03	7.44	0.07	3.1
	1033	1033.67	0.67	VS051998	0.05	4.04	0.28	2.71
	1033.67	1035.05	1.38	VS051999	0.10	17.80	0.22	3.1
	1035.05	1037.75	2.7	VS052000	0.03	15.05	0.08	3.42
	1037.75	1039.05	1.3	VS052001	0.02	11.80	0.12	2.97

A zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
VDD24043C	1039.05	1040.4	1.35	VS052002	0.12	12.50	0.43	3.1
	1040.4	1041.91	1.51	VS052003	0.14	13.10	0.32	2.97
	1041.91	1043.6	1.69	VS052004	0.03	12.35	0.14	3.01
	1043.6	1044.5	0.9	VS052005	0.16	8.97	0.30	3.1
	1044.5	1045.5	1	VS052006	0.01	9.01	0.04	3.1
	1045.5	1046.85	1.35	VS052007	0.01	9.10	0.04	3.1
	1046.85	1048.45	1.6	VS052009	0.00	8.86	0.03	2.93
	1048.45	1050.3	1.85	VS052010	0.03	9.83	0.08	2.94
	1050.3	1051.5	1.2	VS052011	0.00	9.24	0.02	3.1
	1051.5	1052.1	0.6	VS052012	0.01	10.90	0.02	3.1
	1000.35	1001.25	0.9	VS053460	0.58	15.25	0.88	3.34
	1001.25	1002	0.75	VS053462	0.08	12.30	0.12	3.2
	1002	1002.8	0.8	VS053463	0.62	13.90	1.30	3.2
	1002.8	1003.6	0.8	VS053464	0.07	11.95	0.15	3.2
	1003.6	1004.4	0.8	VS053465	0.15	11.10	0.37	3.2
	1004.4	1005.15	0.75	VS053466	0.52	15.55	0.96	3.2
	1005.15	1005.9	0.75	VS053468	1.11	14.90	2.18	3.09
	1005.9	1006.6	0.7	VS053469	1.11	14.50	2.10	3.05
	1006.6	1007.4	0.8	VS053470	0.38	11.85	0.68	2.94
	1007.4	1008.3	0.9	VS053471	0.58	13.00	0.92	2.9
	1008.3	1009	0.7	VS053472	0.31	14.40	0.59	2.9
	1009	1009.65	0.65	VS053473	0.29	15.90	0.52	2.89
	1009.65	1010.8	1.15	VS053474	0.05	10.80	0.11	2.9
	1010.8	1012	1.2	VS053476	0.00	7.92	0.04	2.9
	1012	1012.85	0.85	VS053477	0.04	6.97	0.09	2.82
	1012.85	1013.7	0.85	VS053478	0.04	7.40	0.08	2.9
1013.7	1014.3	0.6	VS053480	1.03	8.17	2.03	2.85	
1014.3	1014.9	0.6	VS053481	0.10	9.20	0.22	2.9	
1014.9	1015.8	0.9	VS053482	0.20	8.01	0.38	2.86	
1015.8	1016.5	0.7	VS053483	0.34	8.31	0.68	2.9	
1016.5	1017.4	0.9	VS053484	0.51	10.75	0.89	3.01	
1017.4	1018.6	1.2	VS053485	0.05	9.64	0.14	2.88	
1018.6	1019.7	1.1	VS053488	0.03	8.84	0.06	3	
1019.7	1021	1.3	VS053489	0.08	7.88	0.16	3	
1021	1022.15	1.15	VS053490	0.13	8.17	0.22	3	
1022.15	1023.1	0.95	VS053491	0.02	9.02	0.04	3	

A zone								
Hole ID	Depth from	Depth to	Sample length (m)	Sample ID	Cu (%)	Fe (%)	Ag (g/t)	Density (g/cm ³)
	1023.1	1024.26	1.16	VS053492	0.02	8.42	0.04	3
	1024.26	1025.15	0.89	VS053493	0.02	9.19	0.02	2.98
	1025.15	1026.1	0.95	VS053494	0.02	9.42	0.04	3
	1026.1	1027	0.9	VS053495	0.01	8.61	0.03	3
	1027	1027.6	0.6	VS053496	0.02	17.25	0.03	3.1
	1027.6	1028.4	0.8	VS053498	0.02	17.25	0.05	3.1
	1028.4	1029.6	1.2	VS053499	0.20	12.75	0.29	3.1
	1029.6	1030.6	1	VS053500	0.21	13.70	0.88	3.14
	1030.6	1031.9	1.3	VS053501	0.09	10.70	0.13	3.1
	1031.9	1033.6	1.7	VS053502	0.05	10.45	0.10	3.1
	1033.6	1036.3	2.7	VS053503	0.12	12.00	0.22	3.09
	1036.3	1039.05	2.75	VS053504	0.15	12.75	0.28	3.1
	1039.05	1040	0.95	VS053505	0.87	18.75	1.99	3.1
	1040	1042.6	2.6	VS053507	0.06	11.95	0.15	3.1
	1042.6	1045.6	3	VS053508	0.19	12.25	0.38	3.1
	1045.6	1047.4	1.8	VS053509	0.13	10.85	0.29	3.2
	1047.4	1049.8	2.4	VS053981	0.06	10.35	0.16	3
	1049.8	1052.35	2.55	VS053982	0.02	9.91	0.04	3.07
	1052.35	1054.5	2.15	VS053983	0.01	10.00	0.04	3.05
	1054.5	1055.9	1.4	VS053984	0.24	12.60	0.54	3.1
	1055.9	1057.3	1.4	VS053985	0.03	11.05	0.06	3.1
	1057.3	1058.4	1.1	VS053986	0.05	11.65	0.10	3.21
	1058.4	1058.8	0.4	VS053988	3.69	13.95	10.50	3.25
	1058.8	1060	1.2	VS053989	0.06	11.15	0.12	3.2
	1060	1061.25	1.25	VS053990	0.08	11.90	0.19	3.2
	1061.25	1062.6	1.35	VS053991	0.17	11.80	0.36	3.2
	1062.6	1064.15	1.55	VS053992	0.16	11.30	0.41	3.2
	1064.15	1065.15	1	VS053993	0.27	12.90	0.51	3.2
	1065.15	1066.45	1.3	VS053995	0.71	12.65	1.05	3.27
	1066.45	1067.9	1.45	VS053996	0.14	16.70	0.29	3.2
	1067.9	1069.45	1.55	VS053997	0.06	12.85	0.15	3.15
	1069.45	1070.6	1.15	VS053998	0.02	9.97	0.05	3.2
	1070.6	1071.5	0.9	VS053999	1.05	17.35	2.44	3.3

Appendix 3 – References

References

- Ayoglu, Olcay. 2022. “Mineralogical and chemical characterization of magnetite ores in Viscaria, Northern Sweden.” PhD diss., University of Oulu. <https://oulurepo.oulu.fi/handle/10024/20363>
- Bergman S., Kübler L., and Martinsson O. 2001. “Description of regional geological and geophysical maps of northern Norrbotten County (east of the Caledonian orogen).” *Swedish Geological Survey* Ba 56: 1-114. Retrieved from <https://resource.sgu.se/dokument/publikation/ba/ba56beskrivning/ba56-beskrivning.pdf>
- Imana M., Armstrong R., Sandoval D., Jez M., Nkioh E., and Krockert M. 2023. “A geological update on the Viscaria Cu-Fe deposit, Kiruna district, Northern Sweden.” *SGA 17th Biennial Meeting Proceedings* 1: 363–365.
- Martinsson Olof. 1997. “Tectonic setting and metallogeny of the Kiruna greenstones.” PhD diss., Luleå Tekniska Universitet. Retrieved from https://www.researchgate.net/publication/34304651_Tectonic_Setting_and_Metallogeny_of_the_Kiruna_Greenstones
- Pan-European Reserves & Resources Reporting Committee. 2021. “PERC Reporting Standard 2021 for the Reporting of Exploration Results, Mineral Resources and Mineral Reserves.” Retrieved from <https://percstandard.org>
- Tasbicen, Koray. 2022. “Paragenesis and Trace Element Characterization of Sulfides at the Viscaria Cu-Fe Deposit, Kiruna District, Northern Sweden.” Master thesis, New Mexico Institute of Mining and Technology. ProQuest (29995255).
- Tasbicen K., Imaña M., Chávez W.X. Jr. 2023. “Sulfide Mineralogy and Cobalt Department at the Viscaria Cu-Fe Deposit, Kiruna District, Northern Sweden.” *Poster presented at SEG 2023 Conference: Resourcing the Green Transition.*


Appendix 4 – Certificate of Competent Person

CERTIFICATE OF COMPETENT PERSON

As the Competent Person responsible for the information on which the Public Report entitled *Viscaria Exploration Results - PERC (2021) Reporting standard - Table 1 (September 2024)* is based, I hereby state:

- My name is Thomas Lindholm.
- I am an independent consultant to Gruvaktiebolaget Viscaria, Kiruna.
- I am a member of the Fennoscandian Association for Metals and Minerals Professionals as well as a Fellow of the Australasian Institute of Mining and Metallurgy.
- I have a M.Sc. in mining engineering from Luleå University.
- I have worked in minerals exploration and mine development for base metals, precious metals and iron since my exam in 1982.
- I meet the requirements of a 'Competent Person' as defined explicitly in the PERC Reporting Standard.
- Signing of the release of exploration results at Viscaria deposit, including of accompanying documents as PERC Table 1.
- I have visited the site and the mine many times, the first in 1985, while the mine was in full production, the last in September of 2024.
- See PERC Table 1 for Viscaria Exploration results dated 20240924, published on the company's webpage www.viscaria.com.
- I am not aware of any material fact or material change concerning the subject matter of the Public Report that is not reflected in the Public Report, the omission of which would make the Public Report misleading.
- I declare that this Public Report appropriately reflects the Competent Person's view.
- I am independent of Gruvaktiebolaget Viscaria, Kiruna.
- I confirm that I have read all the relevant sections of the PERC Reporting Standard 2021. The Public Report has been prepared under the requirements of the PERC Reporting Standard.
- I do not have, nor do I expect to receive, a direct or indirect interest in the Viscaria mine of the Gruvaktiebolaget Viscaria, Kiruna.
- I have no conflicts of interest in respect of the reporting entity/issuer Gruvaktiebolaget Viscaria, Kiruna or the project/operation.
- At the effective date of the Public Report, to the best of my knowledge, information and belief, the Public Report contains all scientific and technical information required to be disclosed in order to make the Public Report not misleading.

Dated at Luleå and 20240924



Thomas Lindholm. M.Sc. / Senior Mining Engineer, Fellow AusIMM, FAMMP